



OUTER SHEET

SHEET NO. 1 OF 5

SPECIFICATION  
FOR  
SEMICURED CERAMIC SHEET (SCQ-H)

	Checked By
	Drawn by

SPECIFICATION FOR  
SEMICURED CERAMIC  
SHEET (SCQ-H)

Reference : Hitachi Works Dir No. 15W 702-136

CHITPAKARAN  
LOCOMOTIVE WORKS,  
WEST BENGAL, INDIA

  
DY. CEE/TMD

NOLAB235, Rev. - 1  
DATE: 04.09.2004

A C 235

Signature Not  
Verified

Digitally signed by  
Nihar Ranjan Mondal  
Date: 2022.04.11  
16:58:06 +05'30'  
Reason: IIRPS-CRIS  
Location: New Delhi

P-CIM32560  
ALLOCATION SHEET

SHEET NO. 2 OF 5  
DATE

**SPECIFICATION FOR  
SEMICURED CERAMIC  
SHEET (SCQ-H)**

CHITTARANJAN  
LOCOMOTIVE WORKS,  
WEST BENGAL, INDIA

NO.A0235, Rev. - 1  
DATE: 04.09.2009

BY: CEE/TMD

1. Scope:

This specification describes Semicured Ceramic Sheet (SCQ-H) (hereafter abbreviated as sheet) treated with Epoxy Resin to be used for layer insulation of electrical machine.

2. Classification Dimension and Tolerance:

Classification, dimension and tolerance of this tape are given in table - 1.

Table - 1

Description	Nominal thickness (mm)	Nominal width (mm) (a)	Nominal length (m) (b)	Tolerance		
				Thickness (mm)	Width (mm)	Length (m)
SCQ-H: 0.15 x a x b	0.15	(i)450 (ii)410	(i) 36 (ii) 27	+ 0.03 - 0.00	+ 15 0	More than nominal length

NOTE:

Non-standard length may be supplied maximum 10% of total ordered qty. but the length should not be less than 15 m.

3. Quality:

Quality of this sheet is given in table - 2.

4. Shelf-life:

Shelf-life of this sheet is 12 months after mfg. date when kept below 25°C.

5. Test methods:5.1. Resin Content:

One sample of base paper of size: 150 mm x 150 mm is cut and weighed on a balance. Similarly, sample of finished product of same size: 150 mm x 150 mm is taken and weighed. If W1 is the weight of base paper & W2 is the weight of finished product. Resin content (%) =  $\frac{W_2 - W_1}{W_2} \times 100$



The same procedure is repeated for three times and average value is considered for resin content but no individual value should be less than the specified.

SPECIFICATION FOR  
SEMICURED CERAMIC  
SHEET (SCQ-H)

CHITTARANJAN  
LOCOMOTIVE WORKS,  
WEST BENGAL, INDIA

BY: CEE/TMD


NO. 19235, Rev. - 1  
DATE: 04.05.2009

Checked By 
Drawn by 

SHEET NO.4 OF 5

**5.2. Adhesive:**

Two copper strip of size: 125 x 20 x 1.6 mm are taken and one sample of finished Semicured Ceramic Sheet of size 10 x 10 mm are pasted without any external adhesive. 25 mm strip with sheet are under overlap and kept for 5 minutes at 220°C and pressure of 30 kg/cm<sup>2</sup> over overlapping portion. Now, the sample with copper strip is taken out and tensile strength is measured. This process is measured two times and average value is considered as observed value but no individual value should be less than specified.

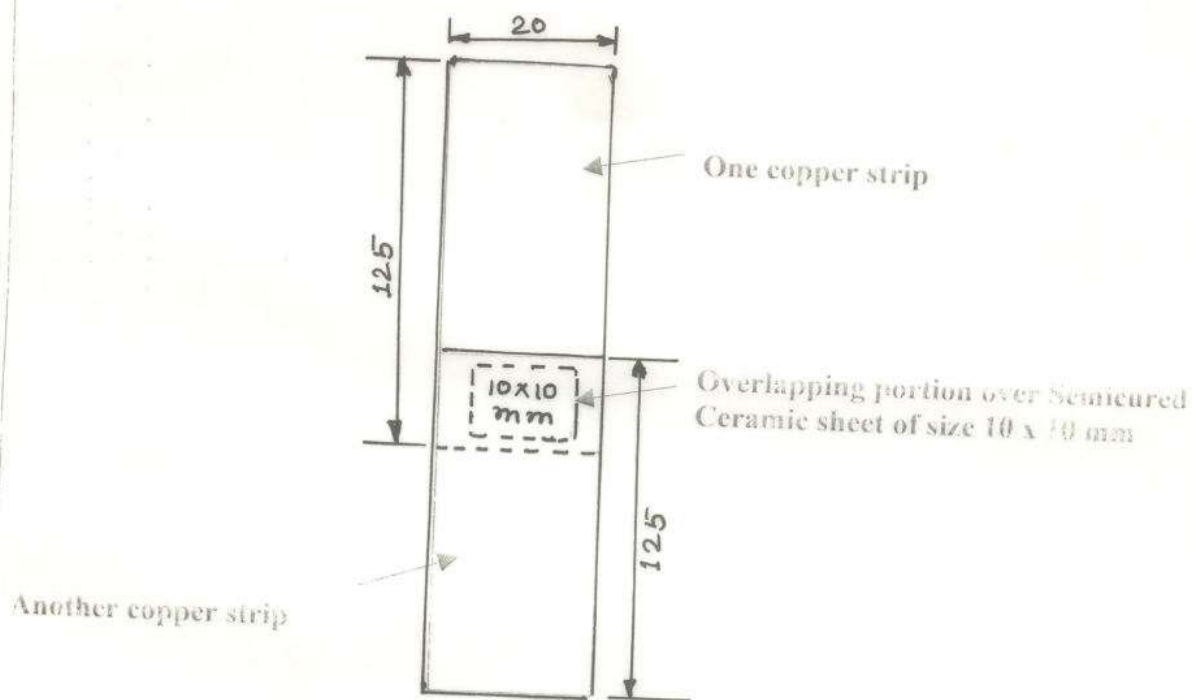

SPECIFICATION FOR  
SEMICURED CERAMIC  
SHEET (SCQ-II)

CHITTARANJAN  
LOCOMOTIVE WORKS,  
WEST BENGAL, INDIA

NG.A0235, Rev. - 1  
DATE: 04.09.2009

BY: CEE/TMD

313801/2024/HEP-CIM32560

Table -2

CIM32560

No.	Item			Unit	Quality	Test procedure	Remarks
01	Weight			g/m <sup>2</sup>	19% ± 25	IS:1060 Pt.1	
02	Resin content			%	29 (+5, -3)	Clause 5.1	
03	Breakdown voltage	Before curing (at one sheet)	Average	kV	≥ 1.0	Clause 13 of JISC2116 & Note No.3	Curing condition: 220°C, 30 kg/cm <sup>2</sup> 5 minutes
			Minimum	kV	≥ 0.8		
		After curing (at two sheets)	Average	kV	≥ 8.0		
			Minimum	kV	≥ 6.0		
04	Tensile strength	Before curing		Kg/15 mm	≥ 2.0	Clause 12 of JISC 2116.	Curing condition same as item 3.
		After curing		Kg/15 mm	> 4.0		
05	Adhesive strength with copper plate			Kg/cm <sup>2</sup>	> 35, at 220°C	As per clause 5.2	Adhering condition: 220°C, 30 kg/cm <sup>2</sup> 5 minutes

## NOTE:

- The cover of different sizes should be of different colour coding as "RED" for item No.1 & "BLACK" for item No.2.
- The length of the spool is made 460 ± 5 mm for item No.(i) and 420 ± 5 mm for item No.(ii).
- The BDV measurement should be taken on at least 10 different points during routine as well as prototype test in lengthwise and widthwise directions as per clause No.13 of JISC 2116.

Checked By

Drawn By

SPECIFICATION FOR  
SEMICURED CERAMIC  
SHEET (SCQ-II)

DY. CHIEF/EMD

CHITTARANJAN  
LOCOMOTIVE WORKS  
WEST BENGAL, INDIA

NO. 4825, Rev. - 1  
DATE: 04.05.2007