

**Enquiry items along with Quantities**

Item No	Size & Item Description	Technical requirement	Quantity in kg	Quantity in Nos. - (Minimum bars)
1	260mm dia X 2700mm Long Round bar	1.5% Ni-Cr-Mo Steel Bar to material specification AA19358 Rev08 in Hot Rolled/Forged, Rough Machined with tolerance on diameter +4/-0 mm only. Hardened & Tempered condition covering all requirements are strictly as per BHEL spec and Ultrasonically tested in accordance with BHEL Standard AA0850118 (Acceptance Category 2). All other details are as per spec AA19358 Rev 08.	26496 kg	(22 Nos)
2	210mm dia X 2100mm Long Round bar		6722 kg	(11 Nos)
TOTAL			33218 kg	

Quantity variation is as per below:

**Item-1:** Supplied quantity is to be restricted between **25234kg** and **26496kg** - Minimum numbers of 22 bars to be mandatory supplied.

**Item-2:** Supplied quantity is to be restricted between **6402kg** and **6722kg** - Minimum numbers of 11 bars to be mandatory supplied.

**Pre-Qualification Criteria:**

Sl. No.	Description of pre-qualification criteria	Vendor response	
		Complied (YES / NO)	Supporting documents required to accept compliance
1	Experience Criteria: 1 year  Bidder should have regularly manufactured and supplied same or similar category products ( <b>Alloy steel round bar of dia 150mm or above</b> ) to any Central / State govt, organization/ PSU/ Publics listed/ Reputed Private company for One (1) number of financial years before the opening date.		PO copies and dispatch details for 01 financial year for the same/similar products in last 5 years from bid opening date.
2.	OEMs and Reseller are allowed to participate in tender. In case of Reseller, valid authorization certificate from OEM to be submitted along with bid.		

**Note:**

1. BHEL has right to verify information / confirmation furnished by asking additional documents, proof etc.

**All the above point-wise pre-qualification requirement are to be necessarily accepted by the bidders for their offers to be considered failing which offers shall be rejected.**

**MAKE IN INDIA format (to be filled by OEMs of the participating bidders)****BHARAT HEAVY ELECTRICALS LIMITED, BHOPAL****MATERIAL MANAGEMENT – STEEL DIVISION**

*For this Procurement, Government of India Public Procurement (Preference to Make in India), Order 2017 with its amendments and subsequent Orders issued by the respective nodal ministries shall be applicable even if issued after issue of this NIT but before finalization of contract/PO/WO against this NIT.*

**As per the Provisions of this order, please submit a self-certification complying with the conditions below on company letterhead duly signed by competent authority.**

I ....., hereby declare on behalf of M/s. .... that we are participating in the Enquiry No./GeM Bid No ..... floated by BHEL, Bhopal (MP), India and shall comply with following:

1. Public Procurement (Preference to Make in India), Order 2017 *with its amendments* and subsequent Orders issued by the respective nodal ministries shall be applicable even if issued after issue of this NIT but before finalization of contract/PO/WO against this NIT.

- (a) A supplier will be treated as **Class-I Local Suppliers**, if the items quoted by bidder have local content equal to or more than 50%.

- (b) '**Local Content**' means the amount of value added in India, which shall be total value of item quoted (excluding net domestic indirect taxes) minus the value of imported content in the item (including all custom duties) as a proportion of the total value, **in percent**.

2. I hereby declare that our firm qualifies as **Class-I Local Suppliers**.

- a. **The Local Content in the items quoted under this Enquiry is ..... Percent**


- b. Details of location(s) in India where this value addition shall be done, is/are as follows:


- (a) .....
  - (b) .....
  - (c) .....

(.....)

For M/s. ....

(Seal & Sign)

 <b>Heat Exchanger Group</b> <b>BHEL Bhopal</b>		<b>STANDARD QUALITY ASSURANCE PLAN (SQAP)</b>							QAP No.		CDE-18-3401		
									Revision No.		00		
		ITEM	<b>ALLOY STEEL FORGED BAR TO AA-19358 (Hardened &amp; Tempered)</b>							Date of Issue		29.09.2018	
										Page		Page 1 of 2	
S.No.	Components & Operations	Characteristics	Category	Type / Method of Check	Quantum of check	Reference Document	Acceptance Norms	Format of Records	Agency			Remarks	
									1	2	3		
1	2	3	4	5	6	7	8	9	10			11	
1.0	<b>IN PROCESS INSPECTION</b>												
1.1	<b>MATERIAL INSPECTION</b>												
a.	Verification of Co-related Mill Test Certificates - MTCs.	<ul style="list-style-type: none"> <li>Chemical composition (Product Analysis)</li> <li>Mechanical Properties</li> </ul>	Major	Visual	100%	BHEL Specification AA-19358 Rev.08	BHEL Specification AA-19358 Rev.08	MTC	R	R	-	<ul style="list-style-type: none"> <li>Hold point of BHEL-IA</li> <li>See Note-b &amp; c</li> </ul>	
b.	Surface Finish	Physical	Minor	Visual	100%	----	----	IR	P	W	-	Bar should be free from any injurious defects.	
a.	Dimensional check	Measurement of Diameter, Length, straightness.	Major	I+Visual	100%	BHEL Specification AA-19358 Rev.08	BHEL Specification AA-19358 Rev.08	IR	P	W	-		
1.2	<b>CHECKING OF FOLLOWING PARAMETERS</b>												
a.	Heat Treatment (in case MTC is silent on the same)	Checking of HT data / Chart	Critical	Visual	100 %	BHEL Specification AA-19358 Rev.08	BHEL Specification AA-19358 Rev.08	IR	P	W	-	<ul style="list-style-type: none"> <li>Calibrated HT furnace need to be used. BHEL-IA to ensure the same while inspection.</li> <li>Witness of HT chart/data only.</li> </ul>	
b.	Ultrasonic Examination	NDT to ensure absence of any volumetric defects	Major	I + Visual	100 %	BHEL Spec. AA-0850118	Cat-2 of BHEL Spec. AA-0850118	IR	P	W	-	<ul style="list-style-type: none"> <li>Calibrated UT meter to be used.</li> <li>UT to be done by ASNT / ASNT Level-II person in UT only.</li> <li>10% of the offered quantity to be witnessed by BHEL-IA.</li> </ul>	
c.	Impact test (In case MTC is silent on the same)	Toughness of material	Major	I + Visual	100%	BHEL Specification AA-19358 Rev.08	BHEL Specification AA-19358 Rev.08	IR	P	W	-	See Note-b only.	
d.	Documentation	Verification of Quality Documents.	Minor	Visual	100% 17	BHEL Specification AA-19358 Rev.08	BHEL Specification AA-10723 Rev.08	Three (03) sets of all the above documents.	P	R	-	<ul style="list-style-type: none"> <li>Out of three sets, minimum one set shall be in original format.</li> <li>See Note-a</li> </ul>	




 <b>Heat Exchanger Group</b> <b>BHEL Bhopal</b>		<b>STANDARD QUALITY ASSURANCE PLAN</b> <b>(SQAP)</b>							QAP No.		CDE-18-3401		
									Revision No.		00		
		ITEM	<b>ALLOY STEEL FORGED BAR TO AA-19358</b> <b>(Hardened &amp; Tempered)</b>							Date of Issue		29.09.2018	
										Page		Page 2 of 2	
S.No.	Components & Operations	Characteristics	Category	Type / Method of Check	Quantum of check	Reference Document	Acceptance Norms	Format of Records	Agency			Remarks	
									1	2	3		
1	2	3	4	5	6	7	8	9	10			11	


**Approval does not relieve supplier from meeting our requirements as per the drawing / specification.**

**Note :**

- (a) All the inspection report & test certificates shall be part of the final QA Document duly signed and stamped by BHEL-IA. Quantity of set = Three (03) Nos. All reports shall be arranged in sequential manner as per this QAP with proper index sheet at top and same to be submitted to BHEL along-with the supply only. Later submission of these reports are not at all acceptable. BHEL-IA to ensure it while giving final dispatch clearance.
- (b) In the absence of original correlated MTC, material to be tested to ensure both chemical & mechanical properties at Govt. Approved Lab / BHEL TSD / manufacturer's lab having calibrated instruments (duly approved by NABL / NABL appointed agency). Sample for check test shall be drawn in consultation with BHEL-IA from each heat & production lot.  
In presence of original co-related MTC : No testing is required, record of the same duly endorsed by BHEL-IA with respect to original one to be furnished. In case of spectrometer for chemical testing, calibration by vendor in presence of BHEL-IA using master calibration blocks (as furnished by OEM) is also acceptable.
- (c) Chemical composition shall comply as specified in Para-10.0 of BHEL-Specification AA-19358 Rev.08 only.
- (d) All other technical requirements as specified in Spec. AA-19358 Rev.08 need to be ensured.

**LEGEND:** 1: Supplier, 2: BHEL IA, 3: Customer; P-Perform, W-Witness, R-Record review, MTC : Mill test Certificates, IR : Inspection report, IA : Inspection Agency, I : Instrument to be used for check.

Prepared by :  Sarvesh Asthana Draughtsman - CDE		Reviewed by :  Santosh Mahto Dy. Manager (D) CDE	Approved by :  S.K. Biswas. Sr. Dy. General Manager (D) CDE
---	--	--	---

	<h1 style="margin: 0;">CORPORATE PURCHASING SPECIFICATION</h1>	<div style="border-bottom: 1px solid black; padding-bottom: 2px;">AA19358</div> <div style="border-bottom: 1px solid black; padding-bottom: 2px;">Rev No. 08</div> <div style="padding-bottom: 2px;">PAGE 1 of 6</div>				
<h2 style="margin: 0;">1.5% NICKEL – CHROMIUM – MOLYBDENUM STEEL FORGINGS – HARDENED AND TEMPERED</h2>						
<p><b>1.0 GENERAL:</b></p> <p>This specification governs the quality requirements of 1.5% Nickel – Chromium – Molybdenum Steel Forgings, Hardened and Tempered.</p> <p>The raw material for these forgings is covered by AA10559</p>						
<p><b>2.0 APPLICATION:</b></p> <p>Suitable for general engineering purposes.</p>						
<p><b>3.0 CONDITION OF DELIVERY:</b></p> <p>Hardened and tempered.</p> <p>Rough machining of the forgings shall be carried out, unless otherwise specified in BHEL order/drawing.</p>						
<p><b>4.0 COMPLIANCE WITH NATIONAL STANDARDS:</b></p> <p>The material shall comply with the following National standards and also meet the requirements of this specification.</p> <p>IS: 4367 – 1991 : Alloy steel forgings for general industrial purpose. Gr: 40Ni6Cr4Mo3, H&amp;T</p>						
<p><b>5.0 DIMENSIONS AND TOLERANCES:</b></p> <p>The dimensions and tolerances shall be as specified in BHEL order/drawing. Wherever these are not specified, the machining allowances and tolerances shall be as specified below.</p> <table style="width: 100%; border: none;"> <tr> <td style="width: 40%;">For finish machined drawings</td> <td style="width: 60%;">: 3 ± 1 mm</td> </tr> <tr> <td>For rough machined drawings</td> <td>: ± 1 mm</td> </tr> </table>			For finish machined drawings	: 3 ± 1 mm	For rough machined drawings	: ± 1 mm
For finish machined drawings	: 3 ± 1 mm					
For rough machined drawings	: ± 1 mm					
<p><b>6.0 MANUFACTURE:</b></p> <p>Forgings shall be manufactured from steel produced by the open electric, arc furnace, there after refined by vacuum degassing or other process as may be agreed to between BHEL and the manufacturer.</p>						
Revisions: Cl: 33.1.0, A.3 of MRC -FCF+HTM		<b>APPROVED:</b> INTERPLANT MATERIAL RATIONALISATION COMMITTEE – MRC(FCF+HTM)				
Rev No.08	Amd No.	Reaffirmed				
Dt:30-01-2008	Dt:	Year:2014				
Prepared HEP, Bhopal		Issued Corp.R&D Dt. of 1 <sup>st</sup> Issue February, 1979				

# CORPORATE PURCHASING SPECIFICATION



Steel shall be fully killed.

Sufficient discard shall be made from each ingot to ensure freedom from pipe, segregation and other defects.

The amount of hot working and finishing temperature shall be such as to ensure complete soundness and adequate uniformity of structure and mechanical properties after heat treatment. The forgings shall not be over heated.

The minimum reduction ratio when forgings are made out of ingots shall be 4:1

For sizes above 250mm ruling section the minimum reduction ratio shall be 3.5:1

**Note:** Raw material like Ingots/Blooms/Billets required for forgings should be procured from BHEL approved sources along with test certificate.

## 7.0 HEAT TREATMENT:

Forgings shall be hardened and tempered to give the mechanical properties specified.

Stress relieving of the forgings shall be done so that minimum residual stresses are leftover.

## 8.0 FINISH:

As mentioned in the drawing.

## 9.0 FREEDOM FROM DEFECTS;

Forgings shall be free from defects such as cracks, flakes, seams, segregation, harmful non-metallic inclusions and other defects which may affect the utility of the forgings.

## 10.0 CHEMICAL COMPOSITION:

The melt analysis of steel and permissible variation in the composition of the forgings from the melt analysis shall be as specified below:

Element	<u>Melt analysis</u> <u>percent</u>		<u>Permissible variation percent</u>	
	Min.	Max.	Upto 250 mm	>250 upto 500 mm
Carbon	0.35	0.45	± 0.02	± 0.04
Silicon	0.10	0.35	± 0.03	± 0.04
Manganese	0.40	0.70	± 0.04	± 0.06
Nickel	1.25	1.75	± 0.05	± 0.05
Chromium	0.90	1.30	± 0.05	± 0.06
Molybdenum	0.20	0.35	± 0.03	± 0.04
Sulphur	---	0.035	+ 0.005	+ 0.010
Phosphorus	---	0.035	+ 0.005	+ 0.010



# CORPORATE PURCHASING SPECIFICATION

AA19358

Rev No.08

PAGE 3 of 6

## Note:

- 1) Wherever necessary, more restricted ranges of chemical composition may be specified subject to mutual agreement between BHEL and the manufacturer.
- 2) Elements not quoted above shall not be added to the steel, other than for the purpose of finishing the heat and shall not exceed the following limits:

Element	Percent, max
Copper	0.25
Vanadium	0.05
Tin	0.05

## 11.0 TEST SAMELES:

- 11.1** Unless otherwise specified in the order/drawing, test samples shall be taken from each melt and each heat treatment batch. Test samples should be cut from the heat treated forgings by cold process only and shall receive no further heat treatment.

Test samples shall be taken from locations indicated on the drawing, leaving enough material, if required, for testing at BHEL's end, integral with the forging.

Test samples shall be cylindrical or rectangular in shape and cut at a distance of 12.5 mm below the heat treated surface.

- 11.2** When integral test pieces are not called for, a test sample equivalent to the ruling section or 65 mm diameter, whichever is less and 610 mm long, having similar reduction ratio and heat treatment, as the forgings it represents shall be provided per heat, per heat treatment batch for check testing at BHEL along with the forgings. The sample shall be properly identified and correlated with the heat/heat treatment Batch No/Test certificate No., Test samples shall be taken at a distance of 12.5 mm below the heat treated surface.
- 11.3** Test samples shall generally be taken in the longitudinal direction. However, for economic reasons or where the size/configuration does not permit the same. Test samples may be taken in the transverse or radial direction. The test sample orientation shall be mentioned in the test certificate.

## 12.0 MECHANICAL PROPERTIES:

The test pieces, after being heat treated as per clause 7.0 above, shall show the following properties upto a limiting section of 800mm. Properties for thicker sections shall be subject to agreement between BHEL and the manufacturer. Test methods are specified below:

# CORPORATE PURCHASING SPECIFICATION

**12.1 Tensile test:**

IS: 1608

**12.2 Hardness test (Brinell):**

IS: 1500

**12.3 Charpy Impact Value:**

IS: 1499

This test applicable for forgings of sizes above 16mm only.

Property	Sample (See Cl: 11.3)	Limiting ruiing section, mm					
		Up to 30	>30 to 63	>63 to 100	>100 to 150	>150 to 250	>250 to 500
Tensile strength N/mm <sup>2</sup>	Longitudinal/	1200	1100	1000	900	900	900
	Transverse/ Radial/Tangential	to 1350	to 1250	to 1150	to 1050	to 1050	to 1050
Yield strength min, N/mm <sup>2</sup>	Longitudinal/ Transverse/ Radial/Tangential	1000	880	800	700	690	690
Elongation on 5.65√S <sub>0</sub> gauge length percent, min	Longitudinal	10	11	13	13	13	13
	Transverse	5	6	7	7	7	7
	Radial	6	7	9	9	9	9
	Tangential	7	8	10	10	10	10
*Hardness Brinell,HB	----	355 to 399	325 to 370	295 to 341	266 to 311	262 to 311	262 to 311
Impact Value (ISO – U on 3 samples) min., Joules	Longitudinal	20	28	32	37	34	28
	Transverse	10	14	16	19	17	14
	Radial	12	17	19	22	20	17
	Tangential	15	21	24	28	26	21

\* **Note:** Hardness test can be conducted only, when tensile test cannot be performed.**13.0 ULTRASONIC TEST:**

Each forging shall be tested ultrasonically in accordance with BHEL standard AA0850118 to ensure freedom from internal defects. The norms of acceptance shall be as per Category 2 of the above standard.





# CORPORATE PURCHASING SPECIFICATION

AA19358

Rev No.08

PAGE 5 of 6

## 14.0 ADDITIONAL TESTS:

If specified in the drawing/order, the following tests shall be conducted:

- i) Magnetic particle test.
- ii) Any other tests.

Norms and acceptance shall be as specified in the drawing/order.

## 15.0 TEST CERTIFICATES:

Three copies of test certificates shall be supplied unless otherwise stated in the order, preferably in the test certificate format annexed to this specification (Annexure-1).

In addition, the supplier shall ensure to enclose one copy of the test certificate along with their dispatch documents to facilitate quick clearance of the material.

The test certificate shall bear the following Information.

Dimensional Inspection.

Details of heat treatment.

Reduction ratio.

Chemical composition including trace elements.

Results of mechanical tests.

Results of ultrasonic test.

Results of additional tests called for in the order/drawing.

## 16.0 PACKING AND MARKING:

Forgings shall be suitably packed to prevent corrosion and damage during transit. Machined surfaces shall be properly protected with anti-corrosive compounds. Each package or forging (when supplied separately) shall be legibly marked with the following Information:

AA19358:1.5% Nickel – Chromium – Molybdenum Steel Forgings –Hardened and Tempered  
BHEL Order No.:

Consignment/Identification No.:

Weight:

Melt. No.:

Batch No.

Supplier/s name

## 17.0 REFERRED STANDARDS (Latest publications including amendments):

1. AA0850118      2. IS: 1500      3. IS: 1608      4. IS: 1757      5. IS: 4367

AA19358

Rev No. 08

PAGE 6 of 6

# CORPORATE PURCHASING SPECIFICATION



## ANNEXURE - 1

### RECOMMENDED TEST CERTIFICATE FORMAT FOR FORGINGS

#### SUPPLIER'S NAME AND ADDRESS TEST CERTIFICATE FOR FORGINGS

- |   |  |
|---|--|
| 1. Customer:                              | 9. Reduction Ratio } Ingot to Bloom<br>Bloom to Blank        |
| 2. TC No. & Date:                         | 10. Batch No.:   |
| 3. PO No.:                                | 11. Heat/Melt No.  |
| 4. Process of Melting Ingot:              | 12. Spec. No.  |
| 5. Deoxidisation Process:                 | 13. Test Bar Size & Nos.                                     |
| 6. Forging Method:                        | 14. Supplier of the ingot/billet/<br>Bloom and TC reference. |
| 7. BHEL's Reference for Approval of Bloom |  |
| 8. Discard: Top _____%; Bottom _____%     |  |

#### 15. FORGINGS COVERED BY TEST CERTIFICATE

S.No.	Drawing No. & Item No.	Description	Quantity & Weight

#### 16. CHEMICAL COMPOSITION (PERCENT)

Element	C	Si	Mn	S	P										
As Per Specn.	Min.														
	Max.														
Actual Values															

#### 17. HEAT TREATMENT (To be accompanied by Recorder Chart, Whenever called for)

Condition	Heating Rate, °C/hr.	Temp. °C	Soaking Time, Hrs.	Cooling Rate, °C/hr	Cooling Medium

#### 18. MECHANICAL PROPERTIES

As Per Specn.	Min.	Max.	T.S. N/mm <sup>2</sup>	Y.S. 0.5/0.2% Proof N/mm <sup>2</sup>	% Elongation 5.65√S <sub>0</sub> GL	% R.A. Min.	Hardness BHN (Min. 3 values)	Impact Value Joules	Bend Test		
									Angle of bend	Dia of mandrel	Result
Actual Values											

19. SURFACE FINISH (When called for in the order/drg.)

20. DIMENSIONAL INSPECTION

#### 21. NON-DESTRUCTIVE TESTS

Nature of Test	Acceptance level	Instrument used	Range	Results	Any other detail
Ultrasonic					
Radiographic					
Dye penetrant/ Magnetic Particle					

#### 22. METALLOGRAPHIC EXAMINATION (To be conducted if called for and photo micrographs to be attached along with a report)

Location of Sample	Etchant used	Magnification	Constituent observed	Relative %	
Microstructure	Macroetch	Inclusion Rating			

23. OTHER TESTS IF ANY (MICROSCOPIC, SULPHUR PRINTS, ETC)

24. IDENTIFICATION OF FORGINGS AS PER PURCHASE SPEC.

We hereby certify that the items mentioned above have been tested and inspected in our presence and are found to be in accordance with drawings, specifications and purchase order.

SIGNATURE, NAME & SEAL OF THE  
INSPECTING OFFICER  
DATE:

SIGNATURE, NAME & SEAL OF THE  
CHIEF OF QUALITY CONTROL/  
CHIEF METALLURGIST OF THE SUPPLIER  
DATE:

#### INSTRUCTIONS

- Details of all heat treatment processes carried out should be furnished sequentially in 17.
- Test certificates are to be furnished as per Purchase order and specification, in A4 size preferably in transparent paper.
- All the entries including signature should be in block colour ink.
- If testing is done by outside agencies, the original TCs shall be furnished.
- The actual TC may run into more than one A4 size paper, if needed, to facilitate filling up of details.



# CORPORATE STANDARD

AA 085 01 18

REV.No. 01

PAGE 1 OF 6

## ULTRASONIC TESTING, CLASSIFICATION AND ACCEPTANCE STANDARDS FOR STEEL FORGINGS, BILLETS AND BLOOMS

### 1.0 SCOPE:

This standard deals with the ultrasonic testing of steel forgings, billets and blooms. The procedure covers pulse echo direct contact manual ultrasonic flaw detection technique. This standard does not apply to austenitic steel forgings.

### 2.0 PERSONNEL REQUIREMENT:

Personnel performing non-destructive examination and evaluation shall be qualified to the recommended practice SNT - TC - 1A or any other recognised practice.

### 3.0 EQUIPMENT CHARACTERISTICS:

#### 3.1 Frequency range:

The ultrasonic equipment shall be suitable for operating at frequencies within the range of 0.5 to 6 MHz.

#### 3.2 Sensitivity:

The sensitivity of the equipment shall be tested to ensure that the number of full screen back wall echo is not less than that given below, when the appropriate probe is placed on the metalised surface of plastic insert of the Indian Standard reference block (IS:4904)/IIW block.

<u>Frequency range, MHz</u>	<u>Min.No. of full screen back echoes</u>
1	5
2	4
4 to 6	2

#### 3.3 Resolution:

The resolution of the equipment and probe combined shall be such as to show separately indications of the three grooves in the IIW - VI block.

Revision:

C1.9.4 OF MOM OF WG(NDT)

Approved:

INTERPLANT STANDARDIZATION  
COMMITTEE - ( WG-NDT )

Rev.No. 01

Amd.No.

Reaffirmed

Prepared

CFFP  
HARDWAR

Issued  
CORP. R&D

Dt. of 1st issue

Jan '80

Dt. Jan '95

Dt.

Year:

**4.0 SURFACE CONDITION:**

The test surface shall be free from loose scales, rust and such other extraneous material that would interfere with the ultrasonic energy transmission. In case of machined surface, it is desirable to have a surface finish of 6.25 microns or better. A gramophone record type of finish and tear produced by machining tools shall be avoided since these give rise to spurious echoes and cause probe wear.

**5.0 COUPLANT:**

To ensure adequate transmission of ultrasonic energy between the probe and the test object, a suitable couplant having good wetting characteristics such as oil, grease, water, glycerine or cellulose paste shall be used.

**6.0 TESTING TECHNIQUE:**

6.1 Selection of testing technique shall be made after giving due consideration to the method of manufacture and shape of the object tested. Testing technique should be such that each and every part of the object volume is scanned at least once. Successive scans shall overlap a minimum of 15% of the probe width. Uniform contact shall be maintained between probe and object and scanning speed shall not exceed 100 mm/ second. The following techniques are considered to be minimum for providing adequate coverage.

**6.2 Scanning Scheme (Solid And Hollow Forgings):**

Complete length of the forging shall be scanned radially from sides / cylindrical surface through 360° using longitudinal wave probe. Whenever practicable the forging shall be scanned in axial direction also. Hollow forgings, and when necessary, solid forgings also shall be scanned using appropriate shear wave probes to detect axial and radial cracks. Hollow forgings are the forgings made hollow on the press by punching or ring rolling operation.

**6.3 Solid Rectangular Forgings, Billets And Blooms:**

Complete length of the object shall be scanned from two adjacent faces and whenever practicable one end face using longitudinal wave probe.

6.4 Radial cracks on round sections which can not be detected by normal testing method may be subjected to other crack detection methods such as MPI.

**7.0 SCANNING:****7.1 Probes and Frequency:**

Overall scanning shall be done using 2 MHz nominal, 20-25 mm diameter probes except when large grain size and path length make it necessary to use a lower frequency. Smaller probes may be used when necessary. However, for forgings intended for backing material for white metal lined bearings, the examination shall be carried out by 4 MHz probes.



## CORPORATE STANDARD

AA 085 01 18

REV.No. 01

PAGE 3 OF 6

### 7.2 Time Base Calibration:

The time base shall be calibrated using a calibration block or a known dimension of forging under examination.

### 7.3 Sensitivity:

#### 7.3.1 When Calibrated Attenuator Is Not Available:

Reference sensitivity of equipment shall be set such that the maximum acceptable defect equivalent flat bottomed hole in the test block is equal to 75% of the full screen height. Testing shall be carried out at the highest sensitivity possible.

#### 7.3.2 When Calibrated Attenuator Is Available:

The sensitivity of the equipment during scanning shall be set 6 dB more than the sensitivity required to give a full screen height echo from the maximum acceptable size of defect.

Note: The above sensitivity level adjustment is purely for scanning purposes. Once a defect is encountered, the sensitivity shall be brought down to estimate the size of defect for evaluation of the material under test.

## 8.0 ESTIMATION OF FLAW SIZE:

### 8.1 Large Size Flaws:

The size of large flaws can be estimated by moving the probe in all directions and plotting the midpoint of the probe when echo falls to 50 percent or 6 dB.

### 8.2 Small Size Flaws:

#### 8.2.1 When Calibrated Attenuator Is Not Available:

8.2.1.1 The size of the flaw may be estimated by comparing with the echoes of the flat bottomed holes at appropriate depths in a test block of ultrasonically similar material.

8.2.1.2 The size of the flaw may also be estimated by moving probe successively in all the four directions at right angles to each other and plotting the mid point of the probe when echo height falls to 50% or 6 dB. Due allowance shall also be made for beam spread, depth and orientation of flaw and diameter of the forging if the scanning is done from the curved surface.

#### 8.2.2 When Calibrated Attenuator Is Provided With The Equipment:

The size of the flaw (smaller than the beam spread) can be estimated accurately in millimetres of equivalent circular flaw with the help of Krautkramer's DGS (Distance - gain - size) diagram. Method of estimating flaw size using a DGS diagram is given in Annexure - A.



## 9.0 CLASSIFICATION OF FORGINGS, BILLETS AND BLOOMS:

9.1 Forgings, billets and blooms are classified into the following five categories depending upon the defect size admissibility for the purpose of ultrasonic testing:

<u>Category</u>	<u>Unacceptable defects</u>
1	<ul style="list-style-type: none"> <li>(i) Cracks, flakes, seams &amp; laps.</li> <li>(ii) Defects giving indication larger than that from a 2 mm diameter equivalent flaw.</li> <li>(iii) Groups of defects with maximum indication less than that from a 2 mm diameter equivalent flaw which cannot be separated at testing sensitivity if the back echo is reduced to less than 70%.</li> <li>(iv) Defects giving indications of 1 to 2 mm diameter equivalent flaw separated by a distance less than four times the size of the larger of the adjacent flaws.</li> </ul>
2	<ul style="list-style-type: none"> <li>(i) Cracks, flakes, seams &amp; laps.</li> <li>(ii) Defects giving indication larger than that from a 4 mm diameter equivalent flaw.</li> <li>(iii) Groups of defects with maximum indication less than that from a 4 mm diameter equivalent flaw which cannot be separated at testing sensitivity if the back echo is reduced to less than 50%.</li> <li>(iv) Defects giving indications of 2 to 4 mm diameter equivalent flaw separated by a distance less than four times the size of the larger of the adjacent flaws.</li> </ul>
3	<ul style="list-style-type: none"> <li>(i) Cracks, flakes, seams &amp; laps.</li> <li>(ii) Defects giving indication larger than that from a 6 mm diameter equivalent flaw.</li> <li>(iii) Groups of defects with maximum indication less than that from a 6 mm diameter equivalent flaw which cannot be separated at testing sensitivity if the back echo is reduced to less than 40%.</li> <li>(iv) Defects giving indications of 3 to 6 mm diameter equivalent flaw separated by a distance less than four times the size of the larger of the adjacent flaws.</li> </ul>
4	<ul style="list-style-type: none"> <li>(i) Cracks, flakes, seams &amp; laps.</li> <li>(ii) Defects giving indication larger than that from a 10 mm diameter equivalent flaw.</li> <li>(iii) Groups of defects with maximum indication less than that from a 10 mm diameter equivalent flaw which cannot be separated at testing sensitivity if the back echo is reduced to less than 20%.</li> </ul>



- (iv) Defects giving indications of 5 to 10 mm diameter equivalent flaw separated by a distance less than four times the size of the larger of the adjacent flaws.
- 5
  - (i) Cracks, flakes, seams & laps.
  - (ii) Defects giving indication larger than that from a 15 mm diameter equivalent flaw.
  - (iii) Groups of defects with maximum indication less than that from a 15 mm diameter equivalent flaw which cannot be separated at testing sensitivity if the back echo is reduced to less than 10%.

**Note:** Loss of back wall echo not attributable to the presence of defects or geometry and exceeding the limits mentioned in item (iii) of each category of unacceptable defects shall be a cause for rejection.

#### **ANNEXURE - A**

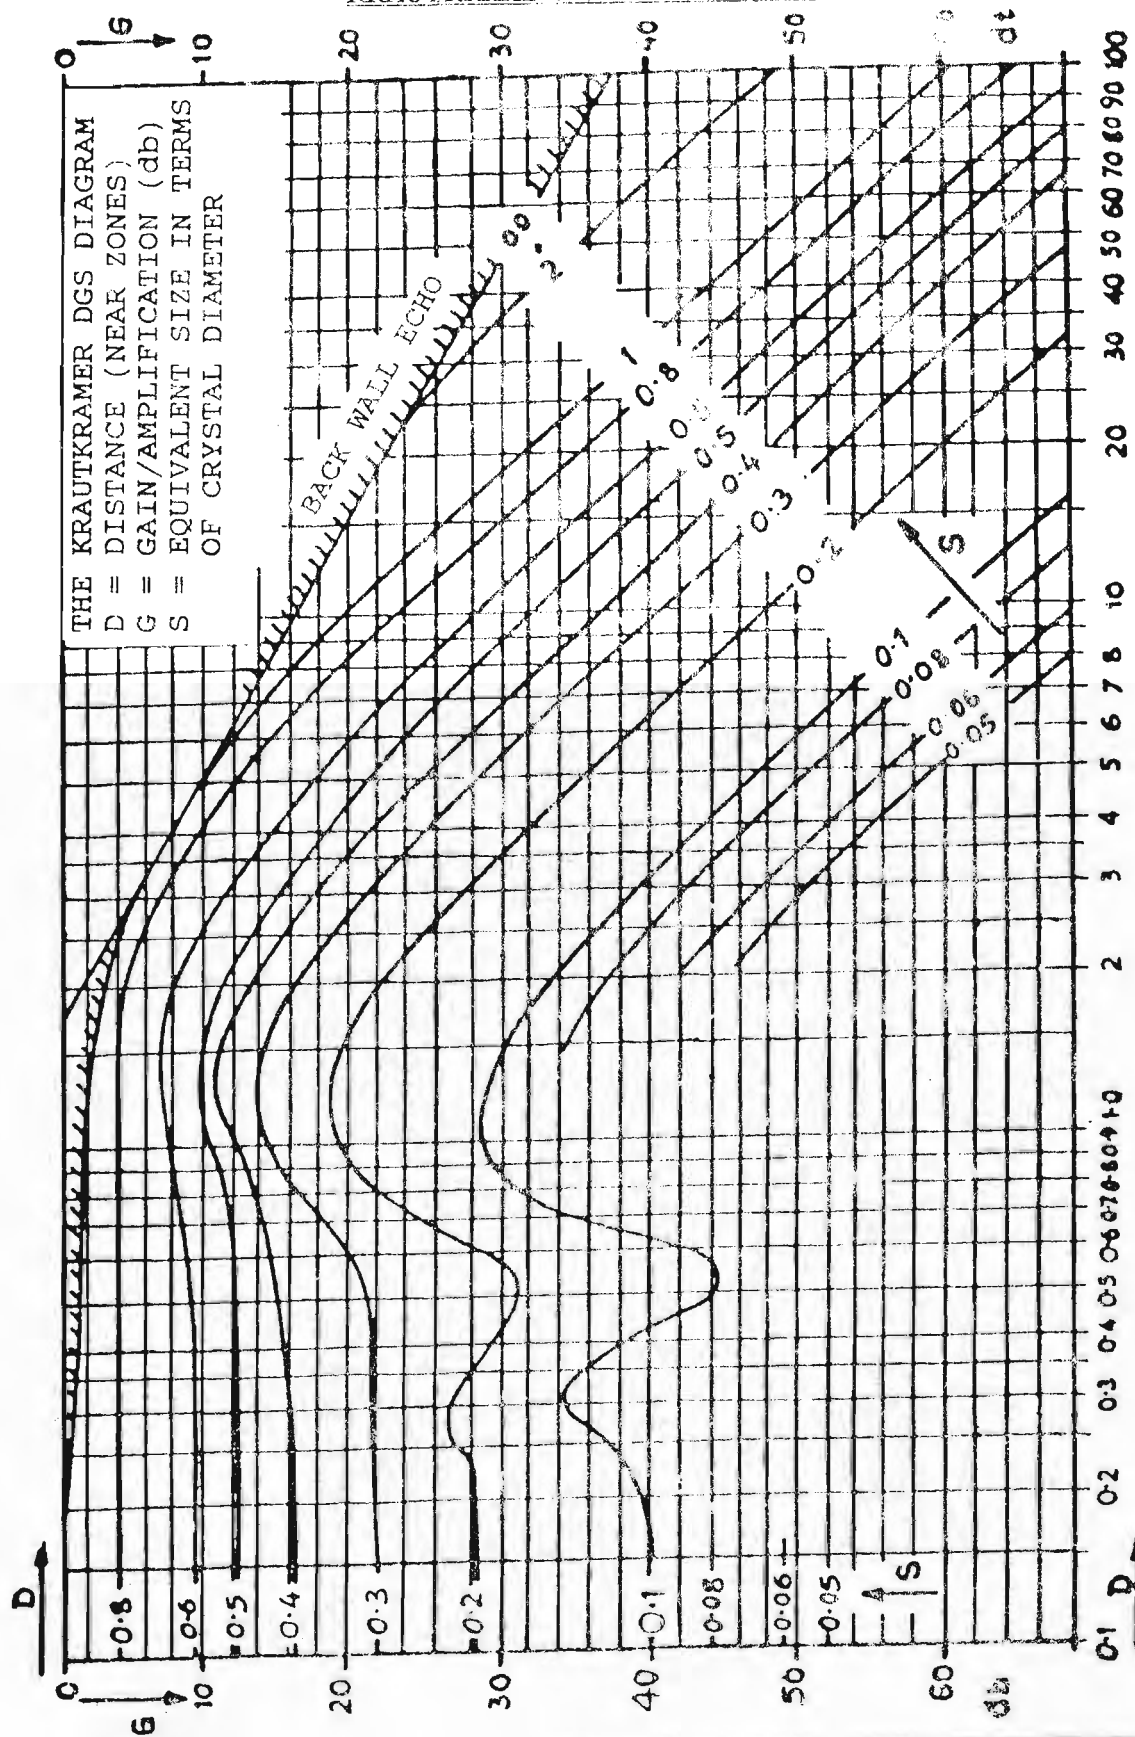
The equivalent flaw size curves of the DGS diagram is prepared by plotting the amplitude in decibels from a series of circular reflectors with increasing distance from the probe in water and so the graph incorporates only the loss in water. When it is found that the attenuation in the material under test is more (this can be checked using back echo curve of DGS diagram), this shall be taken into account while calculating the flaw size. Corrections will not be required for majority of heat treated forgings when tested with 2-4 MHz probes.

A step by step method of estimating flaw size using universal DGS diagram is given below:

- (a) Adjust the depth range of the equipment to the required depth.
- (b) Adjust the back echo to 70% of screen height from a defect free area parallel wall of the material under test or ultrasonically similar test block and note the dB value (A) on the calibrated gain control.
- (c) Mark on the back echo curve of the diagram, the back wall of the distance in terms of near field in millimetres in the case of universal DGS diagram.
- (d) Move the probe to the defective area and get the maximum defect echo. Read off the flaw depth. Increase the gain with the calibrated gain control until echo height reaches 70% of screen height. Note the attenuator reading in dB (B).
- (e) Calculate the gain (G) in dB by subtracting 'A' from 'B'. Count off the gain 'G' downwards from the marked point on the back echo curve, and then move horizontally to intersect the vertical line from the base line corresponding to the flaw depth 'D' in terms of near field in the case of universal diagram.

- (f) Note the equivalent flaw size curve passing through the above point. Multiply the reduced flaw dimension (S) of the curve by the probe diameter to give the equivalent flaw size in millimetres.

ANNEXURE - A  
KRAUTKRAMER'S DGS DIAGRAM





**Annexure-1****DECLARATION (To be given by Bidder)****GeM Bid No.....****Item Description: Round bar of Día 210 mm and 260 mm confirming to specification AA19358**

With reference to above reference bid, we M/s..... (Bidder's Name)  
confirm/declare the following.

1. Quoted Make-.....
2. We are OEM or Reseller - .....
3. Valid OEM Authorization certificate with OEM's Contact Details attached (In case of reseller) - Yes / NA .....
4. We confirm Nil deviation from NIT.

**NOTE:**

1. Preferably material should be make of reputed manufactures like (a) M/s LLOYD, (b) M/s RINL (c) M/s SAIL (d) M/s ESSAR etc.
2. OEM details such as name, designation, address, e-mail Id and Phone number required to be furnished along with the technical bid. (also refer ATC clause).

**(Bidder Seal & Sign)**

## **COMPLIANCE CERTIFICATE**

[To be submitted by participating bidder selecting either option (A) or (B)]

**PI NO. 141140101 / GeM Bid No.** \_\_\_\_\_

**ITEM:** Round bar of Dia 210 mm and 260 mm confirming to specification AA19358

**SPECIFICATION / TDC: - AA19358**

**[A] NO TECHNICAL DEVIATION:**

We confirm to comply enquiry technical specification requirements as per Specification / TDC AA19358 including Standard AA0850118 & QAP CDE-18-3401 without any deviation.

**OR**

**[B] TECHNICAL DEVIATION:** as listed below

**(Deviations listed elsewhere shall not be considered)**

1.....

2.....

3.....

Name of bidder:

Sign & stamp: