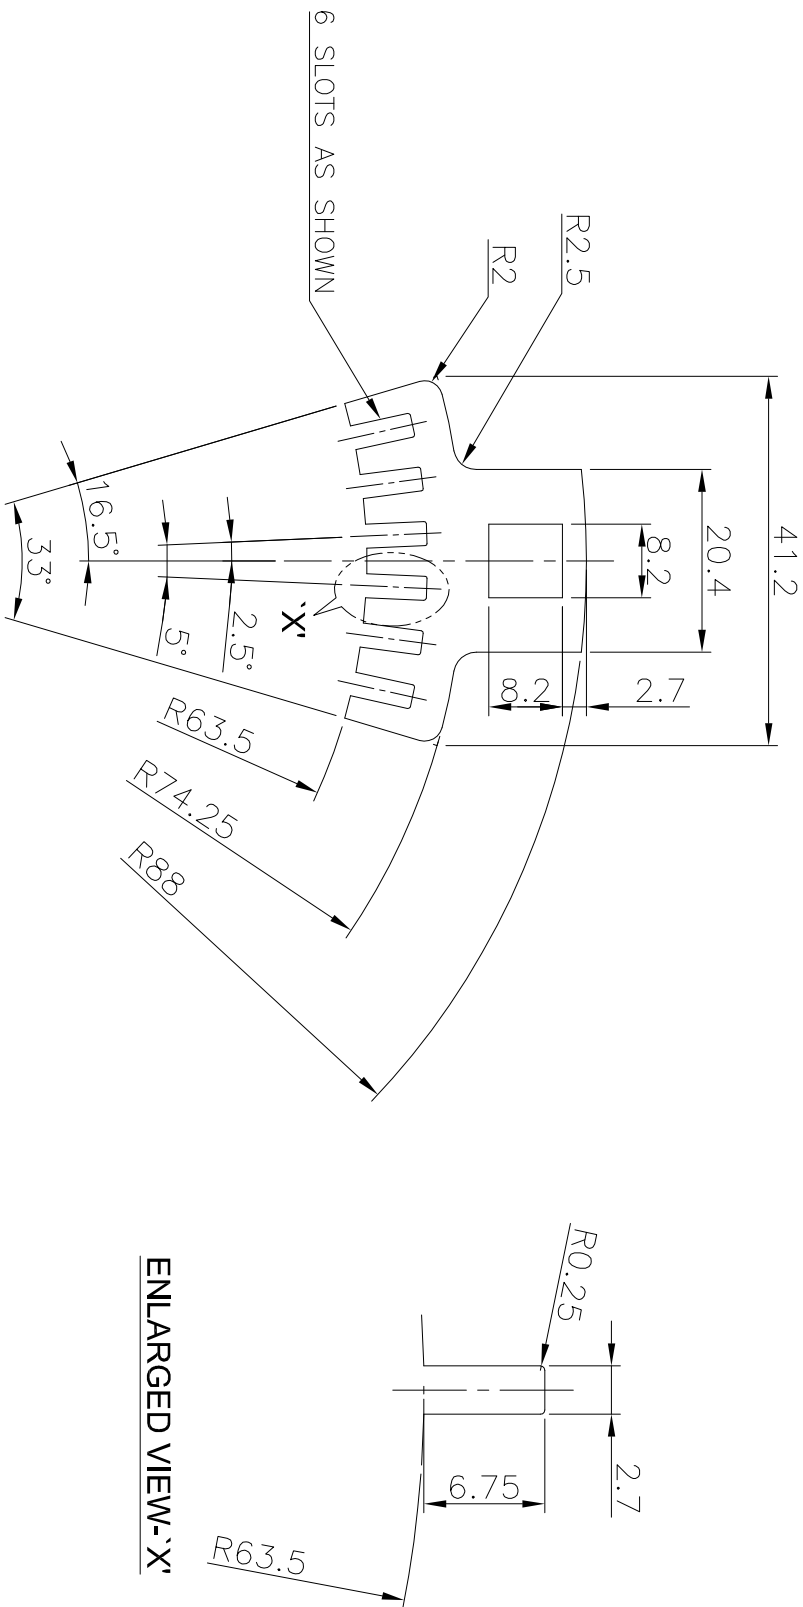



DRG. NO.-3 446 32 99 074



THE INFORMATION ON THIS DOCUMENT IS THE PROPERTY OF BHARAT HEAVY ELECTRICALS LIMITED.  
IT MUST NOT BE USED DIRECTLY OR INDIRECTLY IN ANY  
WAY DETRIMENTAL TO THE INTEREST OF THE COMPANY.

REF. DRG. NO.										SIGN. & DATE										INVENTORY NO.									

	<b>CORPORATE PURCHASING SPECIFICATION</b>			AA 224 15	
				Rev. No. 02	
				PAGE 1 OF 5	
<b>EPOXY LAMINATED GLASS FABRIC BASE SHEET (TEMPERATURE INDEX 155)</b>					
<p><b>1.0 GENERAL:</b></p> <p>This specification governs the quality requirements of laminated sheet made from layers of fine and plain woven glass fabric (non-alkaline glass type E) having suitable silane/volan finish with good electrical properties using thermosetting epoxy resin as the bonding medium. The material has a temperature index of at least 155.</p>					
<p><b>2.0 APPLICATION:</b></p> <p>This material may be used with discretion for insulating spacers, wedges, packers and pressed parts of electrical machines.</p>					
<p><b>3.0 COMPLIANCE WITH NATIONAL STANDARDS:</b></p> <p>The material shall comply, in general, with the requirements of the following standards and also meet the requirements of this specification.</p> <p>NEMA-LI-1: 1989, Gr. G-11.</p>					
<p><b>4.0 DIMENSIONS AND TOLERANCES:</b></p>					
<p><b>4.1 Sizes:</b></p> <p>Thickness, width and length shall be as stated on BHEL order.</p>					
<p><b>4.2 Preferred thickness (mm):</b></p> <p>0.5, 1, 1.5, 2, 3, 4, 5, 6, 8, 10, 12, 15, 20, 25, 30, 40, 50 and 70. Other thickness can also be ordered.</p>					
<p><b>4.3 Tolerances:</b></p>					
<p><b>4.3.1 Thickness:</b></p> <p>Thickness of the sheet shall not depart at any point from the nominal thickness by more than the appropriate value as shown in the following table:</p>					
<b>Revisions :</b> <b>CI: 32.4.43 of MOM of MRC-E</b>			<b>APPROVED :</b> INTERPLANT MATERIAL RATIONALISATION COMMITTEE-MRC ( E )		
Rev. No. 02	Amd.No.	Reaffirmed	Prepared	Issued	Dt. of 1st Issue
Dt:15.01.2003	Dt :	Year :	HYDERABAD	Corp. R&D	May, 1980

AA 224 15	CORPORATE PURCHASING SPECIFICATION	
Rev. No. 02		
PAGE 2 OF 5		

Thickness, mm		Permissible variation from nominal thickness, mm
Above	upto & including	
-	0.5	0.10
0.5	2	0.20
2	3	0.25
3	5	0.50
5	7	0.75
7	10	0.90
10	15	1.10
15	20	1.25
20	25	1.40
25	30	1.50
30	40	1.75
40	50	2.00
50	60	2.50
60	70	3.00

#### 4.3.2 Width and Length:

Size, mm	Tolerance, $\pm$ mm
Below 1000	35
Above 1000	50

#### 4.4 Flatness (for sheets 3.0mm and above):

The flatness of sheets shall be such that when a sheet is placed without restraint on a flat surface, concave side, if present, up, departure at any point of the surface from a light straight edge laid in any direction upon it shall not exceed the following:

- 0.50 mm under a 300 mm straight edge.
- 3.00 mm under a 600 mm straight edge.
- 6.00 mm under a 1000 mm straight edge.

#### 5.0 FINISH:

The surface of the sheets shall be even, smooth, free from visible defects like blisters, loose fibres, resin concentration, delamination, wrinkles, local deformation and dents. The materials shall be supplied with trimmed edges.

#### 6.0 TEST METHODS:

Unless otherwise specified the tests shall be conducted in accordance with the relevant methods of BHEL standard AA 085 17 01.



## CORPORATE PURCHASING SPECIFICATION

AA 224 15

Rev. No. 02

PAGE 3 OF 5

### 7.0 SAMPLING AND ACCEPTANCE:

#### 7.1 Routine and Acceptance Tests:

Unless otherwise stated, one sheet chosen at random out of every 20 sheets of a supply shall be subjected to routine tests. One sheet of 300 X 300 mm of 10 mm thickness shall be supplied with each consignment.

The arithmetic mean of the test results for an individual test shall meet the requirement of this specification.

The lowest value obtained for any test shall not be less than 90% at the specified value.

#### 7.2 Type Tests:

Type tests shall be carried out at the time of first approval and subsequently once in two years and whenever doubt arises, on the quality of the material.

### 8.0 PHYSICAL PROPERTIES:

8.1 Specific Gravity :  $1.8 \pm 0.1$

8.2 Marten's Heat distortion Temperature (Type test)  
(For thickness 10mm and above) :  $240^{\circ}\text{C}$ , min


8.3 Water Absorption at  $20^{\circ}\text{C}$  for 24 hours (Type test):

Thickness (mm)		Water absorption %, max.
Above	upto & including	
-	1	0.40
1	1.5	0.30
1.5	3	0.20
3	10	0.15
10	25	0.10
More than	25*	0.10

\* Thickness above 25 mm shall be machined to 25 mm keeping one side intact.

#### 8.4 Texture of Glass Fabric:

For laminates upto 20 mm thickness a fine woven glass cloth of 0.18mm thick shall be used. For laminates above 20mm thickness a glass cloth of not more than 0.255 mm thick shall be used. This shall be checked by burning the bonding at  $600^{\circ}\text{C}$  for sufficient time.

AA 224 15	CORPORATE PURCHASING SPECIFICATION	
Rev. No. 02		
PAGE 4 OF 5		

**8.5 Heat Shock Test:**

A specimen of size 100x100 of ordered thickness is kept in an oven maintained at 250±5<sup>0</sup> C for 15 minutes. The specimen is removed directly to ambient conditions (ie. Room temperature) after this period and observed. The material is considered satisfactory in this test, if no delamination, cracks, splitting, blistering or resin oozing is observed at the end of the test.

**9.0 MECHANICAL PROPERTIES:**

**9.1 Tensile Strength (For sheets 1.5 mm thick and above) (Type test):**  
250 N/mm<sup>2</sup> (25.5 kg/mm<sup>2</sup> ), min.

**9.2 Cross Breaking Strength (For sheet 1.5 mm thick and above):**

**9.2.1 As received condition:** 350 N/mm<sup>2</sup> (35.6 kg/mm<sup>2</sup> ), min.

**9.2.2** After heating at 150<sup>0</sup>C for 1 hour and tested at 150<sup>0</sup>C. The reduction shall not be more than 50% of the value obtained in received condition.

**9.3 Shear strength (for sheets 1.5 mm thick and above) (Type test):**  
100 N/mm<sup>2</sup> (10.2 kgf/mm<sup>2</sup>), min.

**9.4 Compression strength proof (For sheets 5 mm thick & above) (Type test):**  
400 N/mm<sup>2</sup> (40.8 kgf/mm<sup>2</sup>).

**9.5 Impact strength Charpy - Flatwise (For sheets 2.5 mm & above) (Type test):**

Below 10 mm thick	:	75 kJ/m <sup>2</sup> , min.
10 mm thick & above	:	150 kJ/m <sup>2</sup> , min.

**9.6 Splitting load, Edgewise (For sheets 10 mm thick and above ):** 2.94 kN (300 kg), min.

**9.7 Punching (For sheets below 2.5 mm) (Type test):**  
When the sheet under test is pierced in a single operation with a pattern shown in IS: 1998. There shall not be excessive lifting or cracking around the holes.

**9.8 Machinability (For sheets 3.0mm and above) (Type test):**  
The sheet shall be capable of being sawn, milled, drilled and tapped with a M3.5 tap and shall be capable of being shaped in a shaping machine without showing any sign of cracking or chipping.

**10.0 ELECTRICAL PROPERTIES:**

**10.1 Insulation Resistance after 24 hours immersion in water at 27<sup>0</sup>C (Type test):**  
10<sup>4</sup> Megohms, min.



### Technical Pre-Qualification Requirement (TPQR) of MP End Washer

Date: 24.4.25



Technical Pre-Qualification Requirement of Item **MP End Washer** is as under:

Sl. No.	Description	Vendor to comment	
		Complied / Not complied	Supporting relevant document to be submitted
1.	Offered item should be exactly as per enquiry/NIT. (Deviations if any shall be clearly specified)	Yes/No	Deviation (if any)
2.	Experience in preceding 5 years (from original tender opening date) of same/similar* item to Traction machine manufacturer or Indian Railways.  <b>Development/Trial order shall not be considered.</b>	Yes/No	Unpriced PO copy along with supply proof (delivery challan, invoice etc.)
3.	Please specify whether supplier is OEM or agent/distributor/Trader.	OEM/Agent/Distributor/Trader	Authorization required from OEM for Agent / Distributor/ Trader.

**Notes:**

1. Declaration by vendors regarding information / compliance submitted by vendor shall be correct in all respect. In case any deviation/false information is revealed later on, BHEL is free to initiate appropriate punitive proceeding as per prevalent processes and guidelines of company.

2(\*). Epoxy washers shall be considered as similar item.

Prepared By	Approved By
	
(Basant Tamrakar) Sr Mgr/TME	(Vikas Rawatiya) Sr DGM/TME