





FIRST ANGLE PROJECTION

1 402 74 40010

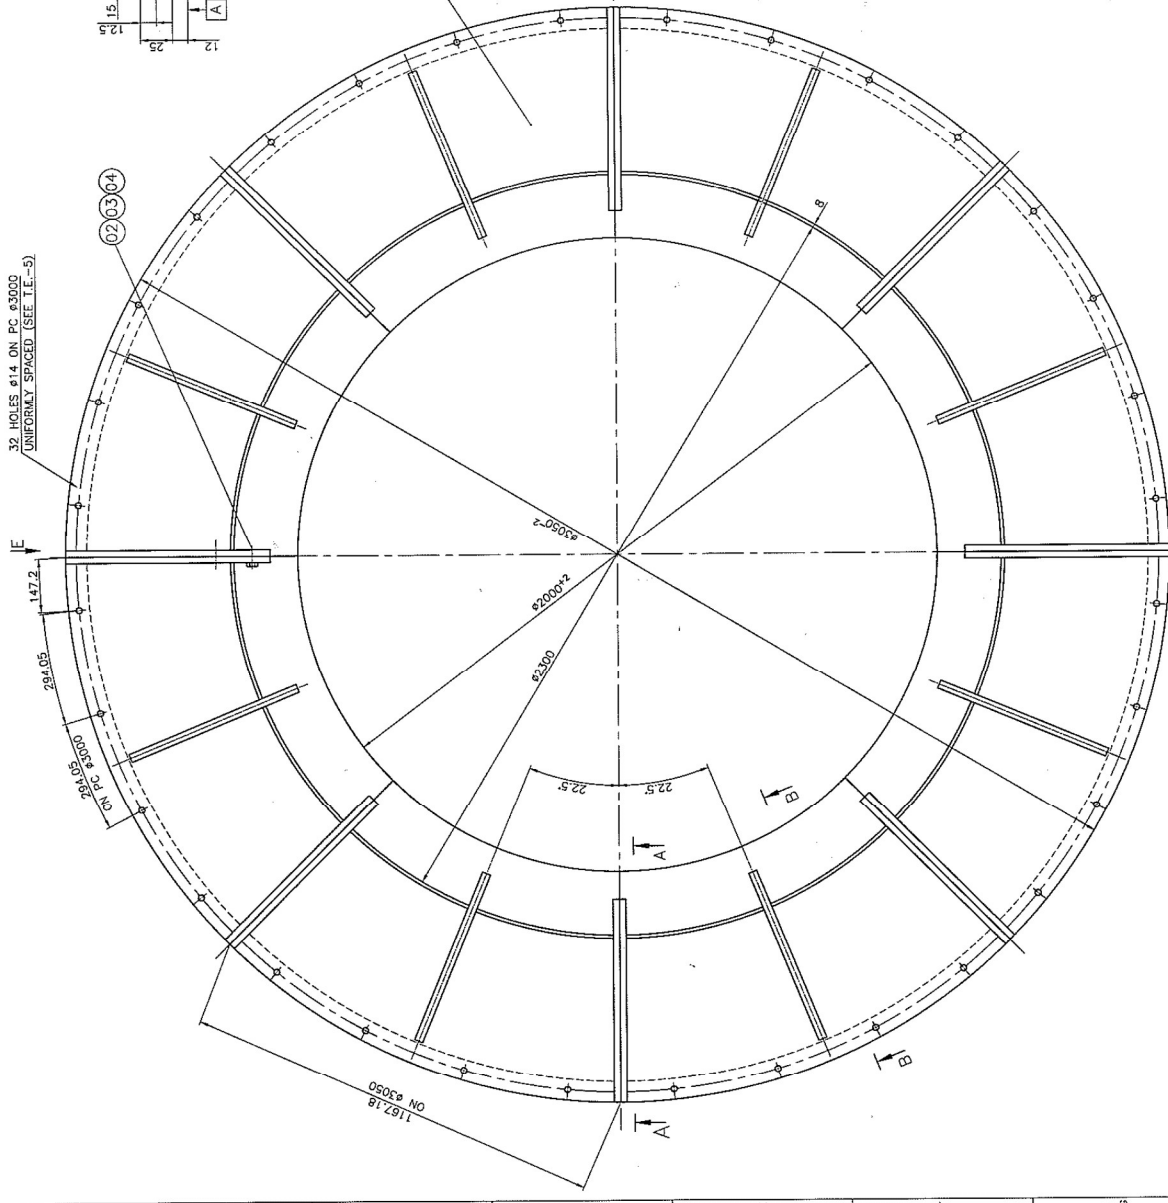

32 HOLES $\phi 14$ ON PC $\phi 2000$ UNIFORMLY SPACED (SEE T.E.-5)

8 GROUPS OF 3 HOLES $\phi 12$ SPOT FACE $\phi 22$

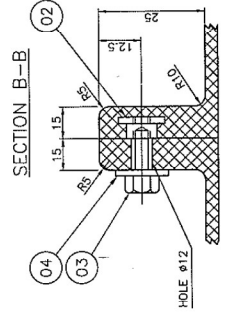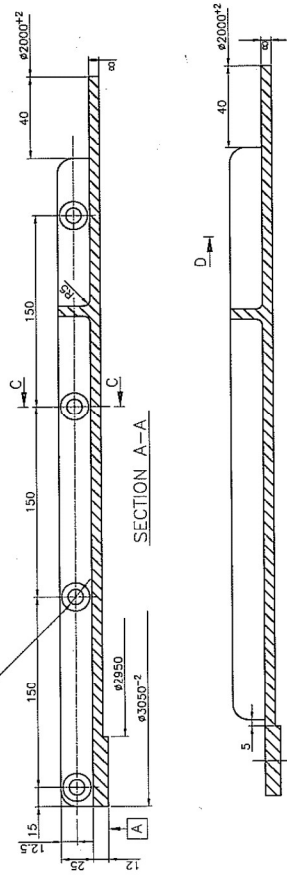

SECTION-DD

SECTION-CC

TECHNICAL REQUIREMENTS

1. THE MOLDING SHALL BE SUPPLIED IN NATURAL COLOUR WITH NO PAINTING OVER AND UNDERNEATH.
2. SHARP EDGES TO BE ROUNDED OFF TO R 0.5 MM.
3. DISPLACEMENT OF HOLES FROM THEIR NOMINAL POSITION SHALL NOT EXCEED 0.5 MM.
4. DURING INSPECTION IT SHALL BE VERIFIED THAT DIMENSION $\phi 2000 \pm 2$ & $\phi 2050 \pm 2$ DO NOT CHANGE BY DISASSEMBLY AND REASSEMBLY OF EIGHT SEGMENTS OF BAFFLE.
5. HOLES $\phi 14$ SHALL BE DRILLED AFTER ASSEMBLY OF BAFFLE SEGMENTS.
6. IDENTIFICATION MARKS ARE TO BE MARKED AT JOINTS TO FACILITATE REASSEMBLY.

| ITEM NO. | QTY | DESCRIPTION | UNIT | WT. | VAL. |
|----------|-----|-------------------|------|-----|------|
| 04 | | WASHER 10.5 STEEL | | | |
| 03 | | SCRU M10X25 LG. | | | |
| 02 | | INSERT | | | |
| 01 | | BAFFLE SEGMENT | | | |

ACQUISITION INFORMATION
 W.O. 48061 A 423-11
 TYPE OF PRODUCT
 M/S XBL - MUMBAI

DISTRIBUTION OF PRINT
 AME -1
 TOX(PLA) -1
 FLA -3

DATE APPROVED
 BY APPROVED

TC 5339-22P
 M/S XBL - MUMBAI

NEETU
 BHOPAL


76

DRAWING NO. 1402744001C 00

BAFFLE ASSY

(ALL DIMENSIONS ARE IN MM)

FIRST ANGLE PROJECTION

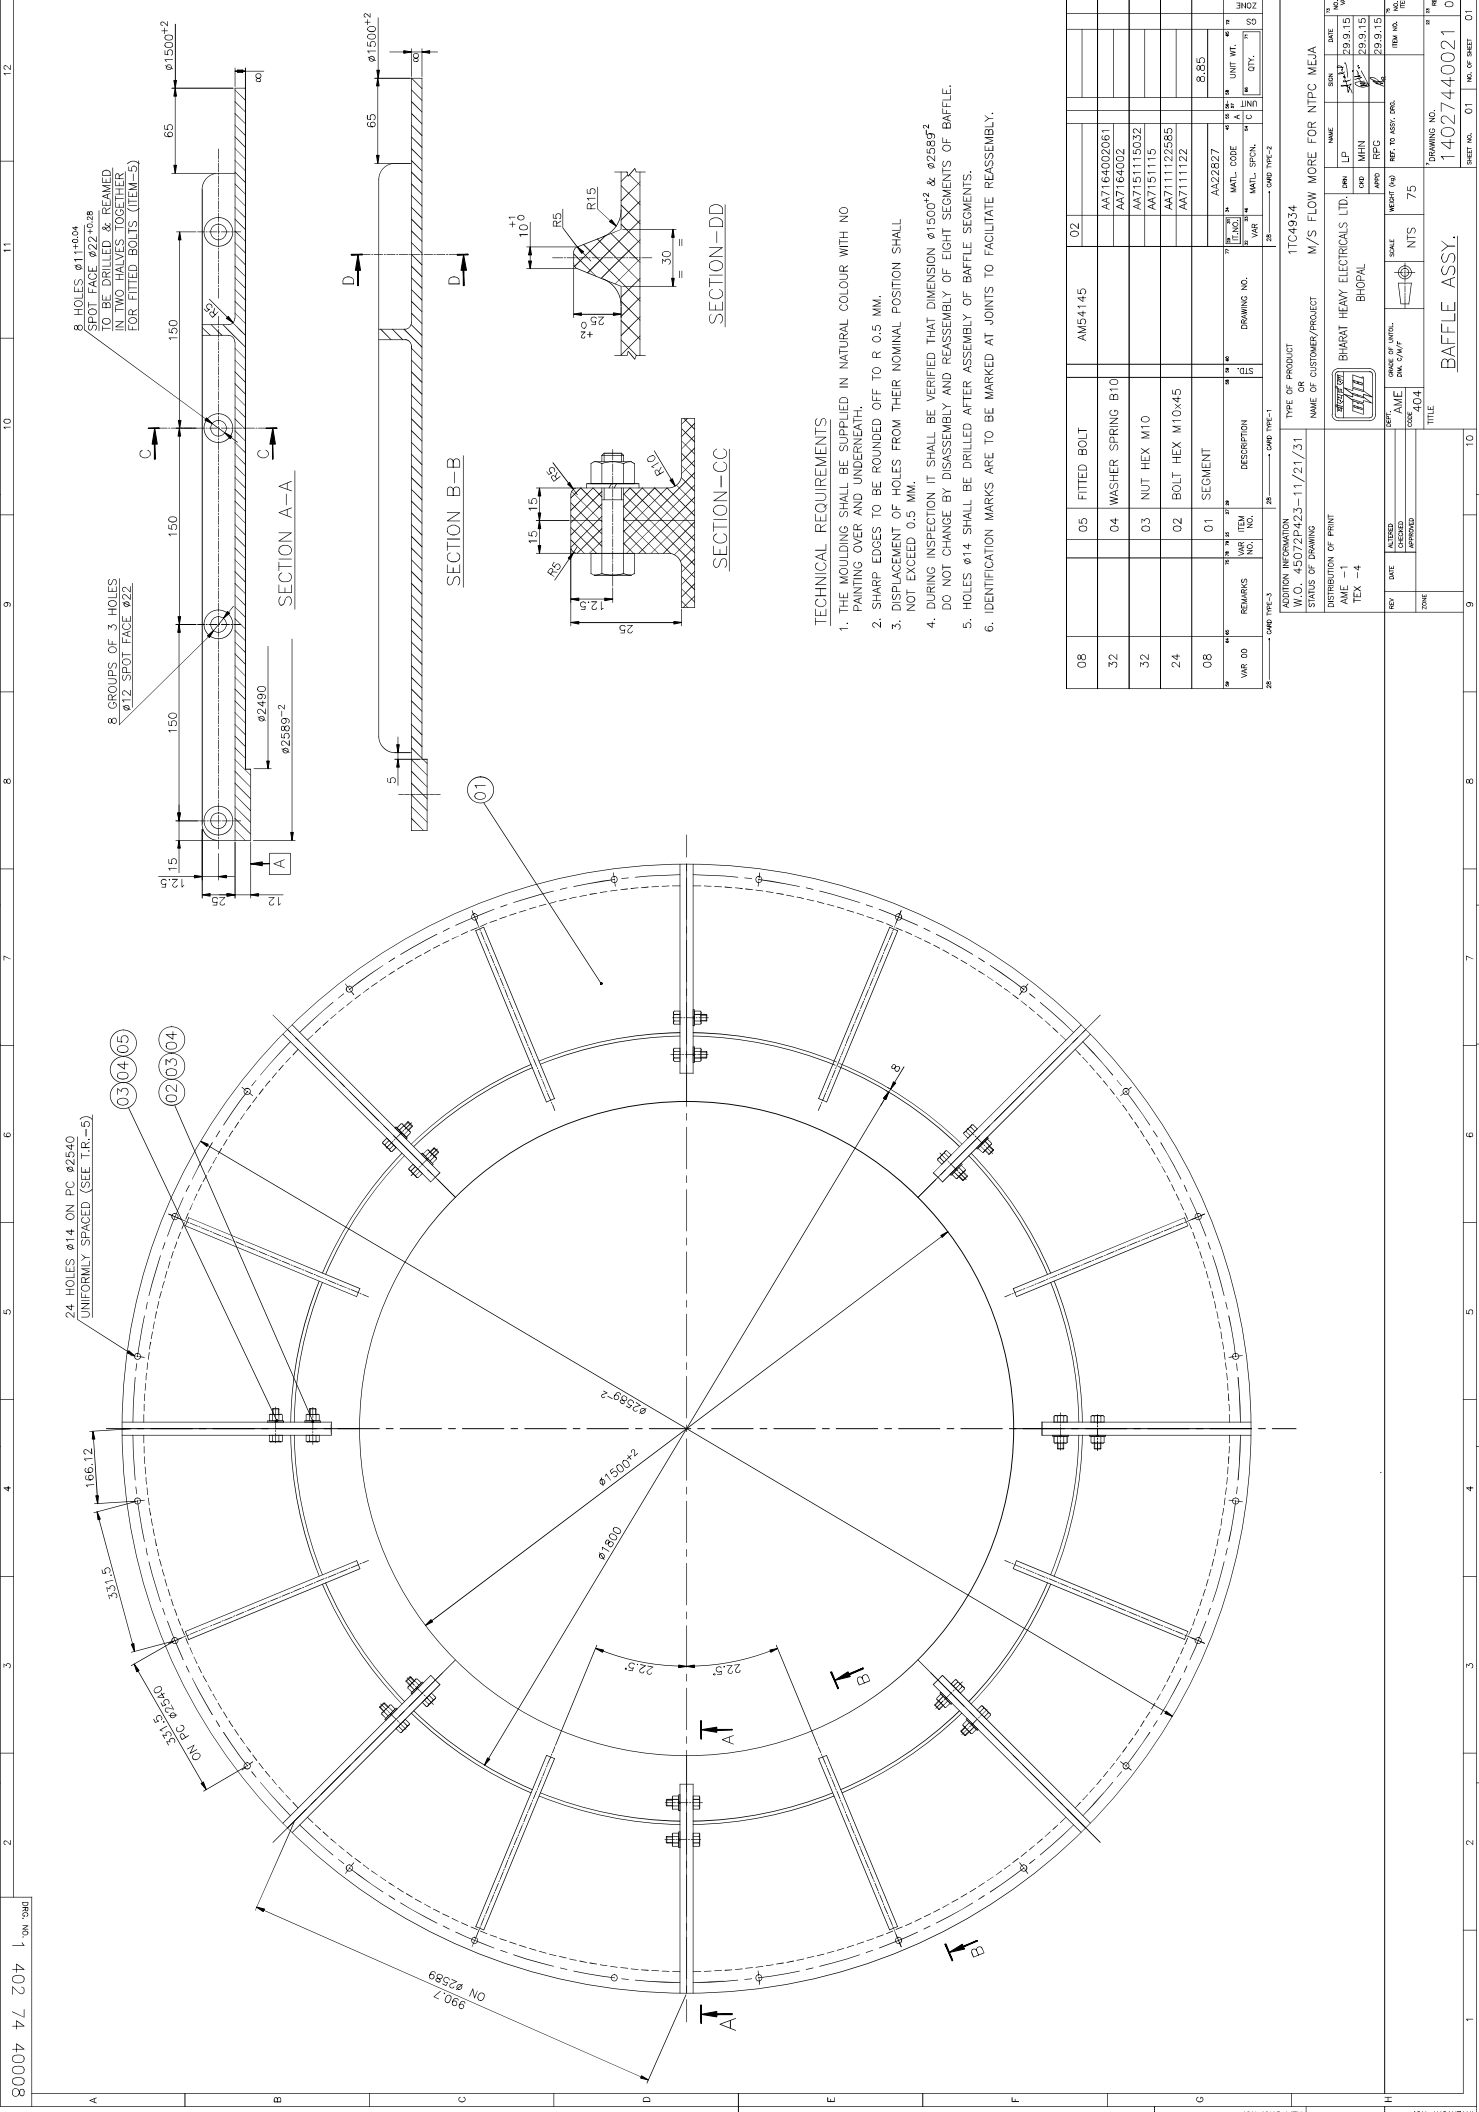

24 HOLES $\phi 14$ ON PC $\phi 2540$ UNIFORMLY SPACED (SEE T.R.-5)

8 HOLES $\phi 110 \times 6$ SPOT FACE $\phi 27 \times 20 \times 6$ IN TWO PLACES TO BE REMARKED IN TWO PLACES TOGETHER FOR FILLED BOLTS (ITEM-5)

8 GROUPS OF 3 HOLES $\phi 12$ SPOT FACE $\phi 22$

SECTION A-A

SECTION B-B

SECTION C-C

SECTION D-D

TECHNICAL REQUIREMENTS

1. THE MOULDING SHALL BE SUPPLIED IN NATURAL COLOUR WITH NO PAINTING OVER AND UNDERNEATH.
2. SHARP EDGES TO BE ROUNDED OFF TO R 0.5 MM.
3. DISPLACEMENT OF HOLES FROM THEIR NOMINAL POSITION SHALL NOT EXCEED 0.5 MM.
4. DURING INSPECTION IT SHALL BE VERIFIED THAT DIMENSION $\phi 1500 \pm 2$ & $\phi 2589 \pm 2$ DO NOT CHANGE BY DISASSEMBLY AND REASSEMBLY OF EIGHT SEGMENTS OF BAFFLE.
5. HOLES $\phi 14$ SHALL BE DRILLED AFTER ASSEMBLY OF BAFFLE SEGMENTS.
6. IDENTIFICATION MARKS ARE TO BE MARKED AT JOINTS TO FACILITATE REASSEMBLY.

| VAR. NO. | REMARKS | VAR. NO. | DESCRIPTION | VAR. NO. | QTY. |
|----------|---------|----------|-------------------|----------|------|
| 08 | | 05 | FITTED BOLT | AMS4145 | 02 |
| 32 | | 04 | WASHER SPRING B10 | | |
| 32 | | 03 | NUT HEX M10 | | |
| 24 | | 02 | BOLT HEX M10x45 | | |
| 08 | | 01 | SEGMENT | | 8.85 |

ADDITION INFORMATION
W.C. 45072423-11/21/31

THESE OF PRODUCT
M/S FLOW MORE FOR NTPC MEJA

OR
NAME OF CUSTOMER/PROJECT
BHARAT HEAVY ELECTRICALS LTD.

DISTRIBUTION OF PRINT
100% FOR T.R.-1
10% FOR T.R.-4

DATE
11/21/31

DESIGNED
4.04

CHECKED
4.04

APPROVED

NAME
SHOPAL

SCALE
75

NTS


DRAWING NO.
14027440021 00

SHEET NO. 01

NO. OF SHEET 01

SIZE A1

(ALL DIMENSIONS ARE IN MM.)

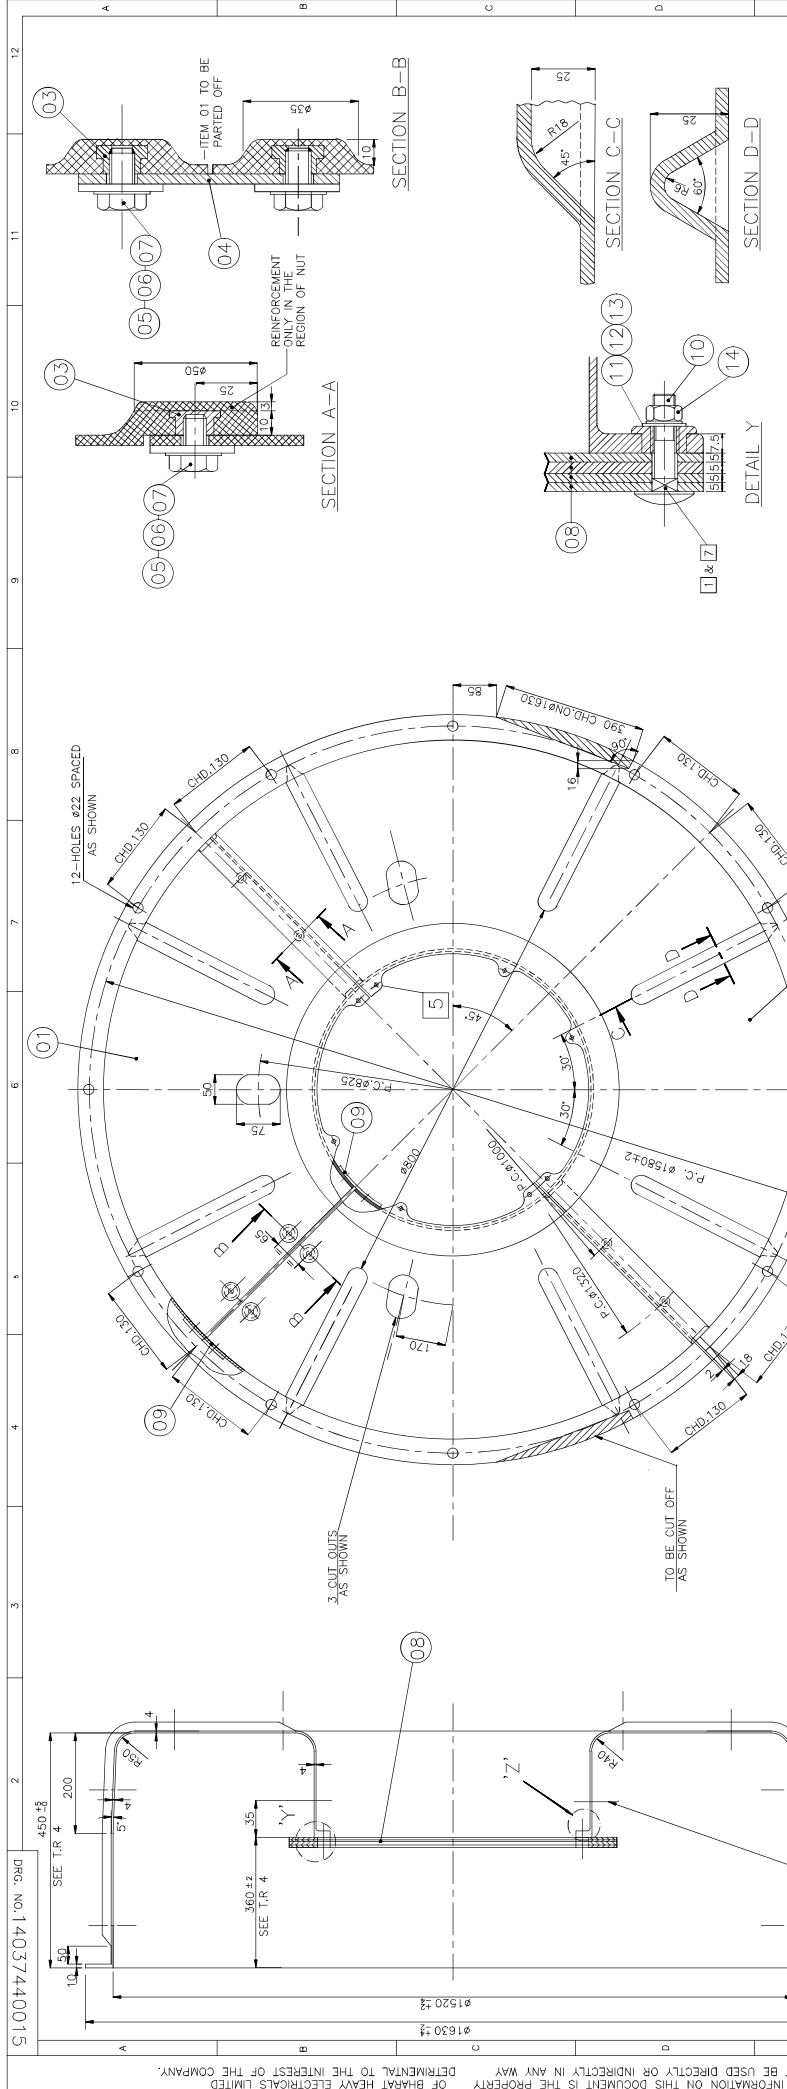


| ITEM NO. | DESCRIPTION | QTY | UNIT | REMARKS |
|----------|--|-----|------|---------|
| 06 | NUT HEX M8 | | | |
| 08 | WASHER SPRING B8 | | | |
| 08 | WASHER M C D 8.4 MM | | | |
| 08 | INSERT AM 54122 | | | |
| 08 | WASHROOM HEAD AM 54121 | | | |
| 03 | SQUARE NECK BOLT 44027442024 | | | |
| 04 | IN 3 PIECES COLLAR SIX AA2221716051 | | | |
| 20 | WASHER SPRING B10 AA22216 | | | |
| 20 | WASHER MCD AM 54109 | | | |
| 20 | SCREW HEX M 10 X 16 AA7121123215 | | | |
| 01 | CUT TO SUIT M 10 X 16 AA7121123 | | | |
| 01 | CLAMP PLATE 44027442024 | | | |
| 20 | INSERT AM 54122 | | | |
| 01 | SHIELD SEGMENT FIBRE GLASS AA22827 | | | |
| 01 | IN TWO PIECES SHIELD SEGMENT FIBRE GLASS AA22827 | | | |

2000 KW SYNCHRONIZER (53692)
M/S TRIVENI ENGG. WORKS FOR NAVA DHATU.


NAME: BHARAT HEAVY ELECTRICALS LTD.
 ADDRESS: BHOPAL
 SCALE: N.T.S.
 TITLE: WINDING SHIELD (D.E.)

DATE: 14.03.2024
 DRAWING NO.: 14037440015
 SHEET NO.: 01 OF 05

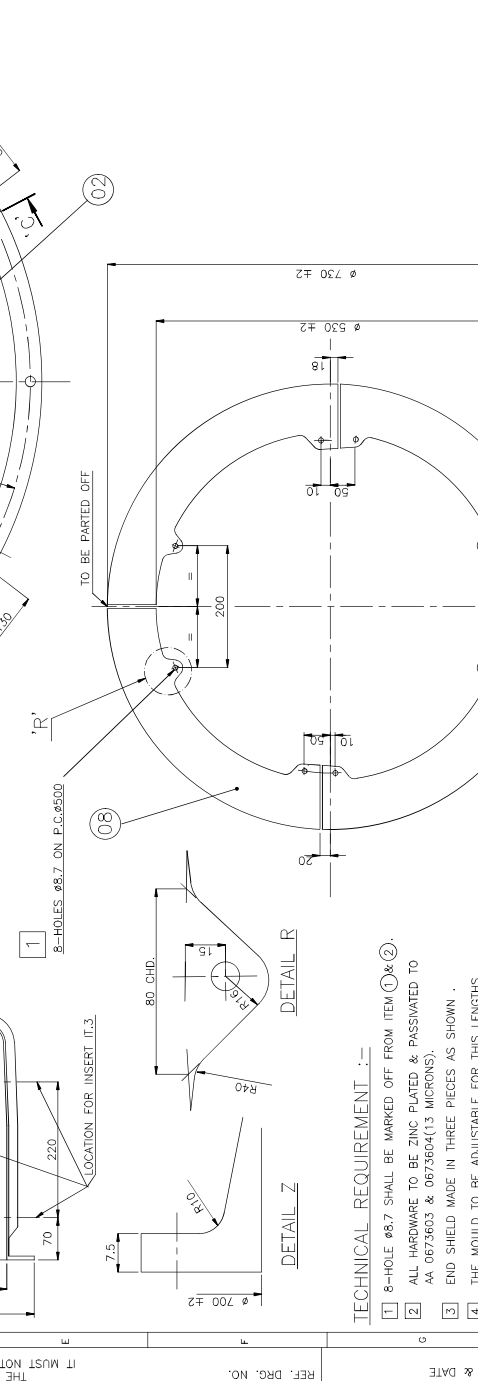

TECHNICAL REQUIREMENT :-

- 8-HOLE Ø8.7 SHALL BE MARKED OFF FROM ITEM ① & ②.
- ALL HARDWARE TO BE ZINC PLATED & PASSIVATED TO AA-0673603 & 0673604 (13 MICRONS).
- END SHIELD MADE IN THREE PIECES AS SHOWN.
- THE WOULD BE ADJUSTABLE FOR THIS LENGTHS.
- INNER FLANGE OF ITS ① & ② TO HAVE SAME SHAPE AS THAT OF IT ⑥.
- TOLERANCE ON THICKNESS ±3, TOLERANCE ON CHORD ±2.
- SQUARE NECK OF IT.10 SHALL BE LOCKED IN Ø8.7 OF IT.08 BY FORMING.

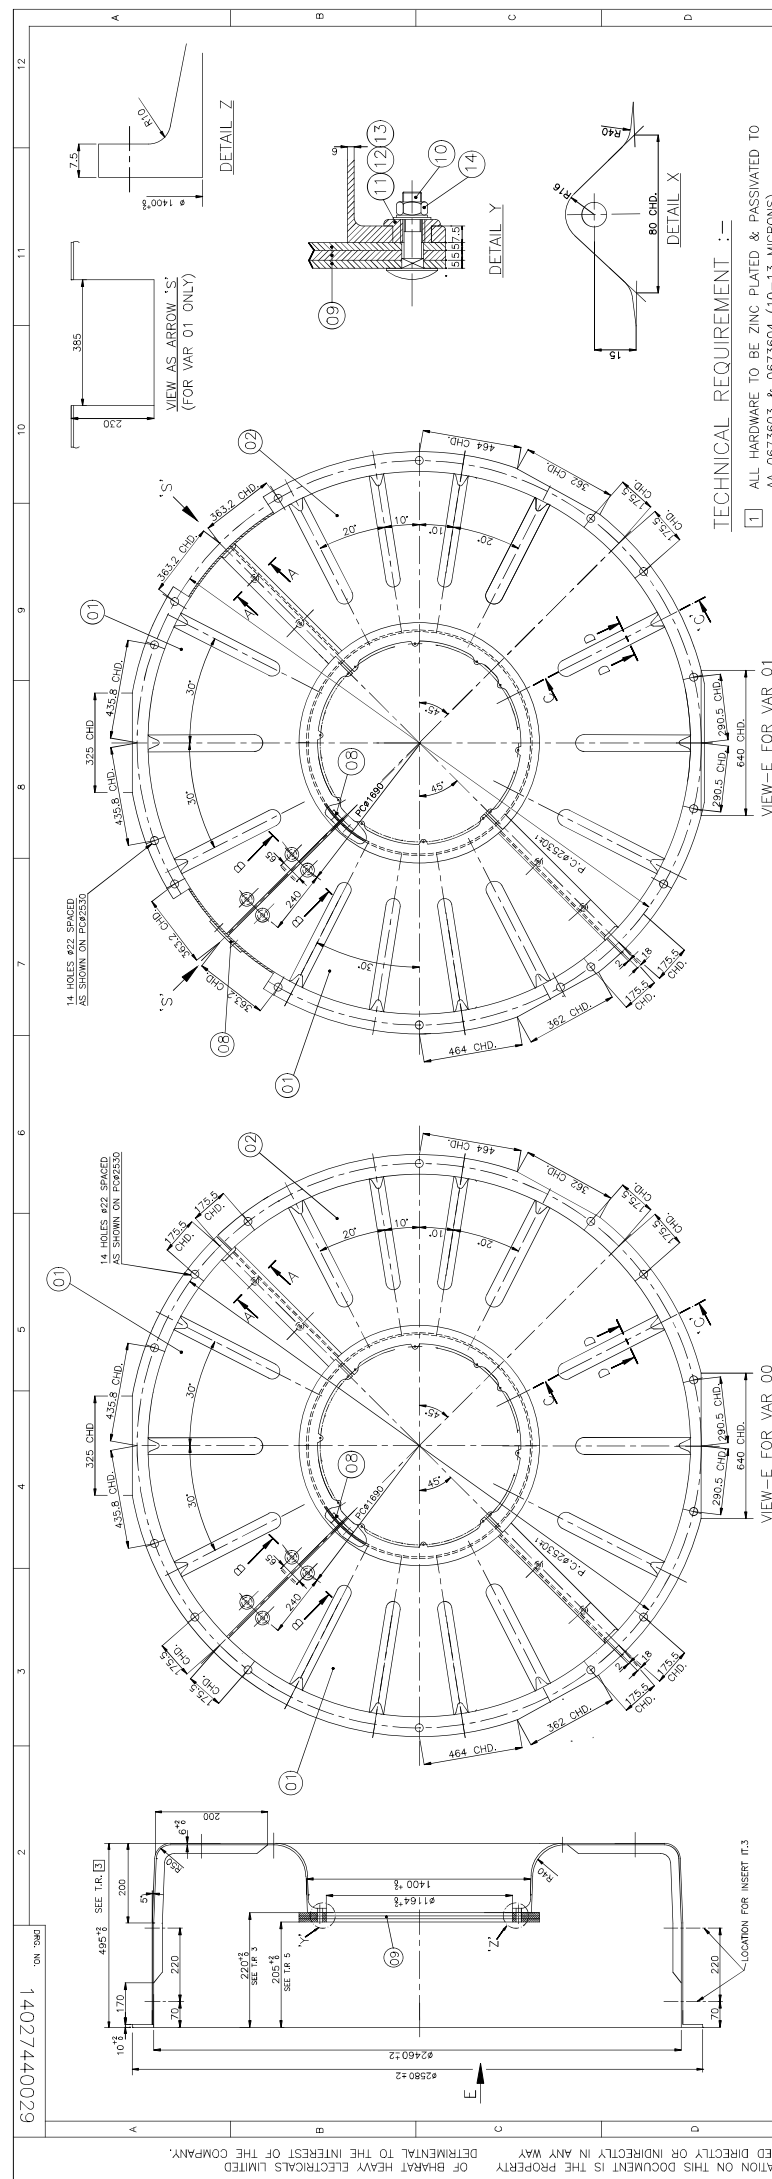

TECHNICAL REQUIREMENT :-

- 1 ALL HARDWARE TO BE ZINC PLATED & PASSIVATED TO AA 0673603 & 0673604 (10-13 MICRONS).
- 2 WINDING SHIELD MADE IN THREE PIECES AS SHOWN.
- 3 THE MOULD TO BE ADJUSTABLE FOR THIS LENGTH.
- 4 12 HOLES $\phi 10.5$ SHALL BE MARKED OFF FROM ITEMS 1 & 4.
- 5 THIS DIMENSION TO BE ENSURED WITHIN LIMITS. THE ID OF WINDING SHIELD MUST NOT BULGE AXIALLY.

| NO. | QTY | DESCRIPTION | REF. NO. | SCALE | DATE | BY | CHKD | APPD | REV. | DATE | REASON |
|-----|-----|--------------------------------|--------------|-------|------|----|------|------|------|------|--------|
| 12 | 12 | NUT HEX M8 | AA7151115024 | | | | | | | | |
| 12 | 12 | WASHER SPRING B8 | AA71511115 | | | | | | | | |
| 12 | 12 | WASHER M C D | AA7164002053 | | | | | | | | |
| 12 | 12 | WASHER 8.4 MM | AA7164002056 | | | | | | | | |
| 12 | 12 | INSERT | AA7164002061 | | | | | | | | |
| 12 | 12 | MUSHROOM HEAD SQUARE NECK BOLT | AA222171R051 | | | | | | | | |
| 03 | 03 | IN 3 PIECES COLLAR | AA22216 | | | | | | | | |
| 02 | 02 | CLAMP PLATE | 44027442025 | | | | | | | | |
| 18 | 18 | WASHER SPRING B10 | AA7164002061 | | | | | | | | |
| 18 | 18 | WASHER MCD | AA7164002 | | | | | | | | |
| 18 | 18 | CUT TO SUIT SCREW HEX M10X16 | AA7121123715 | | | | | | | | |
| 01 | 01 | INSERT | AA7121123 | | | | | | | | |
| 18 | 18 | CLAMP PLATE | 44027442024 | | | | | | | | |
| 03 | 03 | INSERT M10 | AA7121123 | | | | | | | | |
| 02 | 02 | SHIELD SEGMENT FIBRE GLASS | AA22827 | | | | | | | | |
| 01 | 01 | IN TWO PIECES FIBRE GLASS | AA22827 | | | | | | | | |

| REV. | DATE | ALTERED | CHECKED | APPROVED | REASON |
|------|----------|---------|---------|----------|--------|
| 01 | 12.07.19 | | | | |
| 02 | 21.03.20 | | | | |
| 03 | 17.8.22 | | | | |

WEIGHT CORRECTED.

| REV. | DATE | ALTERED | CHECKED | APPROVED | REASON |
|------|----------|---------|---------|----------|--------|
| 01 | 12.07.19 | | | | |
| 02 | 21.03.20 | | | | |
| 03 | 17.8.22 | | | | |

WEIGHT CORRECTED.



CORPORATE PURCHASING SPECIFICATION

AA 22827

Rev. No. 04

PAGE 1 OF 4

FIBRE GLASS REINFORCED POLYESTER MOULDINGS

1.0 GENERAL:

This specification governs the quality requirements of the fibre glass mouldings manufactured by hand lay up process. The mouldings shall consist of cold setting polyester resin reinforced with strands of glass fibre. The glass fibre shall be of Type E (Low Alkali) containing not more than 1% alkali (Na_2O). No filler shall be used in the manufacture of mouldings. The material shall have a temperature Index of at least 130.

2.0 APPLICATION:

Used for roof fuse box and switch gear group cases in traction control gears, insulated baffles of liquid rotor starter in industrial control gears, blower duct, collector duct in turbo generators commutator packing ring, air guides and end support of heavy machines etc.,

3.0 COMPLIANCE WITH NATIONAL STANDARDS:

There is no Indian standard covering this type of material.

4.0 DIMENSION AND TOLERANCES:

Shall be as stated on the order or the drawing accompanying BHEL order.

5.0 FINISH:

Shall have a reasonably smooth surface. The surfaces shall be even, free from visible defects like blisters, cracks, loose fibres, resin concentration wrinkles, local deformation, gas pockets, foreign inclusions and dents etc., and with bond uniformly distributed within the specified limits.

6.0 TEST METHODS:

Unless otherwise specified, the tests shall be conducted in accordance with the order or with the relevant clauses of BHEL standard AA 085 17 01.

7.0 TEST SAMPLES:

Three moulded sheets of size $300 \times 300 \times 3 \pm 0.25$ mm thick and one sheet of 10 ± 0.5 mm thick and of size 300×300 mm prepared from the same batch shall be supplied for test and approval.


Revisions :

Cl: 32.4.53 of MOM of MRC-E

APPROVED :

INTERPLANT MATERIAL
RATIONALISATION COMMITTEE-MRC (E)

| | | | | | |
|---------------|---------|------------|--------------------|---------------------|-------------------------------|
| Rev. No. 04 | Amd.No. | Reaffirmed | Prepared BHOPAL | Issued Corp. R&D | Dt. of 1st Issue Feb, 1980 |
| Dt:15.01.2003 | Dt : | Year : | | | |

| | | | | | | | | |
|--|--|---|------------------|--------------|----------------------|-------------|--|--|
| AA 22827 | CORPORATE PURCHASING SPECIFICATION |  | | | | | | |
| Rev. No. 04 | | | | | | | | |
| PAGE 2 OF 4 | | | | | | | | |
| <p>8.0 PHYSICAL PROPERTIES:</p> <p>8.1 Specific Gravity : 1.6. to 2.0</p> <p>8.2 Water Absorption : 0.8%, max.</p> <p>8.3 Glass Content : 30%, min. Shall be determined by burning the bond at 600⁰C for sufficient time.</p> <p>8.4 Flammability: When tested as per Annexure -1 of the material shall self extinguish within 30 seconds.</p> <p>8.5 Effect of 10% Sodium Carbonate (Na₂CO₃) solution (Optional Test): A sample fo 3 x 75 x 75 mm shall be immersed in 10% sodium carbonate solution (by weight) in water at 80⁰ C for 7 days and then tested for the following physical properties:</p> <table style="width: 100%; border: none;"> <tr> <td style="width: 50%;">Change in weight</td> <td style="width: 50%;">: 1.5%, max.</td> </tr> <tr> <td>Change in dimensions</td> <td>: 1.0%, max</td> </tr> <tr> <td>Surface finish through visual inspection</td> <td>: There shall be no appreciable change in the surface finish. Surface shall be free from defects like pitting, blistering, swelling and deposit etc.</td> </tr> </table> <p>9.0 MECHANICAL PROPERTIES:</p> <p>9.1 Tensile Strength : 100 N/mm², min.</p> <p>9.2 Cross - Breaking Strength : 170 N/mm², min.</p> <p>9.3 Compressive Strength : 160 N/mm², min.</p> <p>9.4 Impact Strength - Charpy-Flatwise - Un Notched: 10 J/cm², min., on 10 mm thick sample.</p> <p>10.0 ELECTRICAL PROPERTIES: Electric Strength In oil at 90⁰C : Proof for 1 minute at 8 kV/mm, flat wise.</p> <p>11.0 THERMAL PROPERTIES: Martin's heat distribution temperature 110⁰C , min., after post curing at 100⁰C for 4 - 6 hours.</p> | | | Change in weight | : 1.5%, max. | Change in dimensions | : 1.0%, max | Surface finish through visual inspection | : There shall be no appreciable change in the surface finish. Surface shall be free from defects like pitting, blistering, swelling and deposit etc. |
| Change in weight | : 1.5%, max. | | | | | | | |
| Change in dimensions | : 1.0%, max | | | | | | | |
| Surface finish through visual inspection | : There shall be no appreciable change in the surface finish. Surface shall be free from defects like pitting, blistering, swelling and deposit etc. | | | | | | | |



CORPORATE PURCHASING SPECIFICATION

AA 228 27

Rev. No. 04

PAGE 3 OF 4

12.0 TEST CERTIFICATE:

Unless otherwise, stated, three copies of test certificates shall be supplied with each consignment, along with the following information:

In addition, the supplier shall ensure to enclose one copy of the test certificate along with the despatch document to facilitate quick clearance of the material.

The test certificate shall bear the following information:

AA 22827: (Rev.No 04): Fibre Reinforced Polyester Mouldings.

BHEL Order No.

Manufacture's/Supplier's Name.

Batch/Lot No.

Quantity Supplied

Date of Manufacturing

Test Results of clauses 4.0, 8.0, 9.0 and 10.0.

13.0 PACKING AND MARKING:

The material shall be packed to avoid contamination and damage in transit. Each container shall be marked with the following information.

AA 22827: Fibre Glass Reinforced Polyester Mouldings.

BHEL order No.

Batch/Lot No.

Manufacturer's/Supplier's Name.

Date of manufacture and expiry.

Quantity supplied.

14.0 REFERRED STANDARDS (Latest Publications Including Amendments) :

1. AA 085 17 01

ANNEXURE - I

TEST METHOD FOR FIRE RETARDANT TEST

1.0 TEST PIECES:

Use five test pieces 10 to 15 mm wide of thickness of the sheet under test. However, if thickness of sheet exceeds 3 mm then thickness shall be reduced to 3 mm keeping one surface intact.

Length of test piece shall be such that the exposed length is 80 mm or more as detailed in figure given below:

AA 228 27

Rev. No. 04

PAGE 4 OF 4

CORPORATE PURCHASING SPECIFICATION

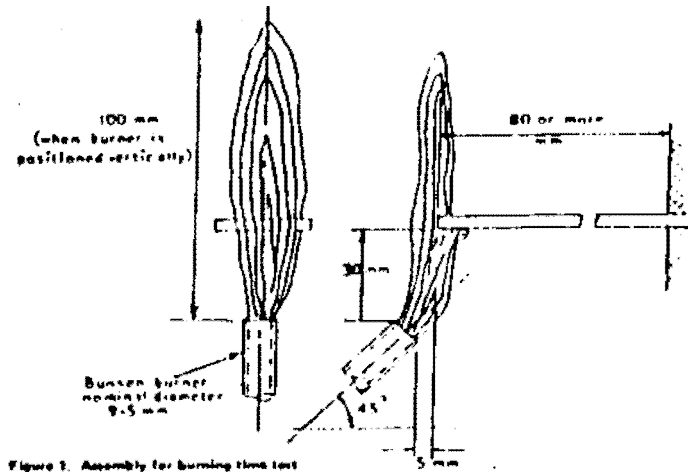


Figure 1. Assembly for burning time test

2.0 CONDITIONING:

Test the material in the as received condition.

3.0 APPARATUS:

The following apparatus is required.

- 3.1 Draught free enclosure that permits observation. For safety and convenience it is desirable that this enclosure be fitted with a device, such as an exhaust fan to remove products of combustion that may be toxic. However, it is important that this device be turned off during the actual test.
- 3.2 Bunsen burner of nominal diameter 9.5 mm and gas supply.
Note: It has been found that for a wide range of materials the character of the flame, i.e. luminous or non-luminous, using common gases, does not affect the result obtained by this method of test.
- 3.3 Installation to fix the test piece and the Bunsen burner in the positions specified.
- 3.4 Stop Watch.

4.0 PROCEDURE:

Clamp the test piece horizontally by one end so that the width dimension is in the horizontal plane. The Bunsen burner should be fixed at an angle of 45° towards the unclamped end of the test piece so that it is 30mm below the bottom edge and 5 mm away from the test piece (see figure).

Adjust the Bunsen-burner, with closed air-ports (see note to 3.2) to produce a flame approximately 100 mm long whilst in the vertical position. Whenever it is desired to ignite the test piece, the burner should be placed in the 45° position described above; it should not be moved during the test (see note below). After 60s turn the burner off. Check the burning time with the aid of the stop watch from the moment at which the flame is turned off. it should extinguish with in 30 seconds.

Note: No burning time can be assigned if, during the 60s ignition period, the test piece distorts away from and out of reach of the flame.



PLANT PURCHASING SPECIFICATION BHOPAL

BP 22893
REV NO. 06
PAGE 1 of 4
**SUPERSEDES
BP22893 Rev05**

HAND MOULDED RANDOM GLASS FIBRE REINFORCED POLYESTER MOULDINGS

1. GENERAL:

This specification governs the quality of Glass fiber mouldings, consisting of a cold setting polyester resin, reinforced with random laid glass fibre made from Type E (low alkali) glass fibre containing not more than 1% alkali (Na₂O). The material has temperature index of at least 130.

2. APPLICATION:

Used for components of A.C. Machines e.g. Commutator Packing Ring, Air guides etc.

3. COMPLIANCE WITH NATIONAL STANDARDS:

There is no Indian Standard covering this of material.

4. DIMENSIONS AND TOLERANCES:

Shall be stated on order or the drawing accompanying the order.

5. FINISH:

Mouthings shall have smooth surface and shall be free from cracks, blisters, gas pockets, foreign inclusions etc. and with bond uniformly distributed.

6. TEST METHOD:

Unless otherwise stated, the tests shall be conducted in accordance with the relevant methods of Corporate Standard AA 085 17 01.

7. SAMPLE FOR TEST:

Two sheets of 5 ± 0.5 mm thickness in the size of 300 x 300 mm shall be supplied for testing and approval.

8. PHYSICAL PROPERTIES:

8.1 Specific Gravity : 1.4 Min.

8.2 Water Absorption : 1.0% Max.

Revision:
Reviewed & brought up to date.

Issued by:

**STANDARDS AND MATERIALS GROUP
TECHNICAL SERVICES DEPARTMENT**

Rev. 06
Date : 29-01-2022
Date of first Issue : June 1986

COPYRIGHT AND CONFIDENTIAL
 The information on this document is the property of Bharat Heavy Electricals Limited,
 It must not be used directly or indirectly in any way detrimental to be interest of the company



TSD 6206.A

PLANT PURCHASING SPECIFICATION BHOPAL

BP 22893

REV NO. 06

PAGE 2 of 4

8.3 Glass Content. : 28 - 43%.

Shall be determined by any conventional method on three test specimens selected at random.

8.4 Fire Retardant Test (Annexure - II) : 30 secs. Max.

9. MECHANICAL PROPERTIES:

9.1 Tensile Strength : 63 N/ mm², Min. (Annexure - I)

9.2 Cross Breaking Strength : 140 N/mm², Min. (Annexure - I)

9.3 Compression Strength : 130 N/mm², Min.

Tests shall be carried out on 2 specimens and both the samples should confirm to the requirement.

10. TEST OF COMPONENTS:

Glass content shall be determined individually on 3 to 5 integral pieces in the components. Integral pieces shall be left at the discretion of the supplier.

Average glass content of 3 to 5 test specimens, as the case may shall be reported and shall meet the requirements of CI.8.3.

11. TEST CERTIFICATE:

Three copies of test certificates shall be supplied with each consignment giving the following information:

In addition, the supplier shall ensure to enclose one copy of test certificate along with their dispatch documents to facilitate quick clearance of the material.

BP 22893 (Rev.06) : Hand Moulded Random Glass Fibre Reinforced Polyester Mouldings.

Our Order No.

Batch/Lot No.

Test values obtained / certificate for compliance for CI.5, 8 & 9.

12. PACKING AND MARKING:

The mouldings shall be suitably packed to avoid contamination and damage in transit. Packages shall be labelled with the following information:

BP 22893: Hand Moulded Random -Glass Fibre Reinforced polyester Mouldings.

Our Order No.

Supplier's / Manufacturer's Name & Grade.

Drawing and item Nos.

Net & Gross Weight.



TSD 6206 A

PLANT PURCHASING SPECIFICATION BHOPAL

BP 22893

REV NO. 06

PAGE 3 of 4

ANNEXURE – I

TENSILE STRENGTH / CROSS BREAKING STRENGTH

Tensile strength / cross breaking strength test shall be carried out as per AA 085 17 01 except for the following.

Test shall be carried out on 5 test specimens irrespective of direction. Thickness shall be measured at five points equally placed to the nearest 0.03 mm in the effective portion of the test piece. This is required to be done due to variation in thickness of sheet because of hand lay up manufacturing method.

Average of these five reading shall be used for calculation purpose.

Tensile strength / cross breaking strength of five test specimens shall be determined. Average result of five test specimens shall be reported as Tensile Strength/cross breaking strength.

ANNEXURE – II

TEST METHOD FOR FIRE RETARDANT TEST

1.0 Test Pieces

Use five test pieces 10 to 15 mm wide, of thickness of the sheet under test. However, if thickness of sheet exceeds 3 mm then thickness shall be reduced to 3 mm keeping one surface intact. Length of test piece shall be such that the exposed length is 80 mm or more as detailed in figure given below: -

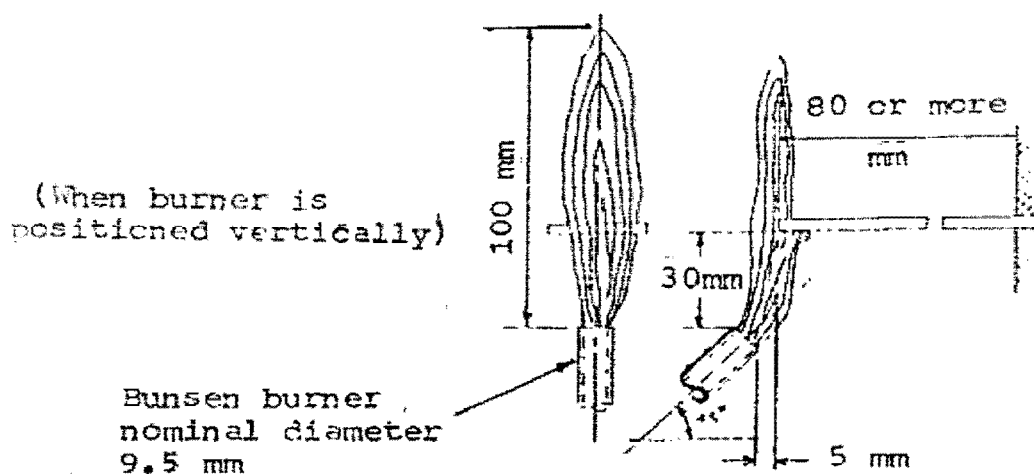


Figure 1. Assembly for burning time test

2.0 Conditioning:

Test the material in the as received condition.



TSD 6206 A

PLANT PURCHASING SPECIFICATION BHOPAL

BP 22893

REV NO. 06

PAGE 4 of 4

3.0 Apparatus:

The following apparatus is required.

3.1 Draught free enclosure that permits observation. For safety and convenience, it is desirable that this enclosure be fitted with a device, such as an exhaust fan to remove products of combustion that may be toxic. However, it is important that this device be turned off during the actual test.

3.2 Bunsen burner of nominal diameter 9.5 mm and gas supply.

NOTE:

It has been found that for a wide range of materials the character of the flame, i.e, luminous or non-luminous, using common gases, does not affect the result obtained by this method – of test.

3.3 installation to fix the test piece and the Bunsen burner in the positions specified.

3.4 Stop Watch.

4.0 Procedure :

Clamp the test piece horizontally by one end so that the width dimension is in the horizontal plane. The Bunsen burner should be fixed at an angle of 45 deg. towards the unclamped end of the test piece so that it is 30 mm below the bottom edge and 5 mm away from the test piece (see figure).

Adjust the Bunsen-burner, with closed air-ports (see note 3.2) to produce a flame approximately 100 mm long whilst in the vertical position. Whenever it is desired to ignite the test piece, the burner should be placed in the 45 deg. position described above it should not be moved during the test (see note below). After 60's turn the burner off. Check the burning time with the aid of the stop watch from the moment at which the flame is turned off.

NOTE:

No burning time can be assigned if, during the 60's ignition period, the test piece distorts away from and out of reach of the flame.

5.0 Expression of Results.

For each of the five test pieces, record the time in seconds from the moment at which the Bunsen flame is turned off until the test piece ceases to burn provided some of the test piece remains unburned. Report the arithmetic mean of the results obtained on the five test pieces as

Burning time of test piece 10 mm to 15 mm wide: ----- seconds.

Alternatively, report if any test piece has burnt away completely, or has distorted away from and out of reach of the flame.