



PLANT PURCHASE SPECIFICATION

(CFFP - HARDWAR)

FF 05066 Rev 5

Page 1 of 7

HEAVY DUTY RESIN BONDED MAGNESIA CARBON BRICKS (RBMC SPL) BRICKS FOR EAF & VAD, VOD & LRF LADLES

1.0 GENERAL:

This specification governs the quality requirements of RBMC-Special bricks for EAF, VAD, VOD & LRF ladles.

2.0 APPLICATION:

- * **Metal and slag zone of Electric Arc Furnaces.** Oxygen lancing is done in EAF for melting and reducing Phosphorous to 0.004%.
- * **Bottom, metal and slag zone of ladles.** Oxygen lancing in ladles during VOD operation.
- * Degassing under vacuum at ≤ 1 Tor for 30 minute at Temp. 1720°C (max) to reduce gas contents and achieve Sulphur $\approx 0.002\%$.
- * Typical final slag composition after secondary refining is as follows: Cao 40-45%, SiO₂ 13- 17%, MgO 10-12%, Al₂O₃ 20-25%, Fe₂O₃ 1.5-3%, Cr₂O₃+MnO <1.2%

3.0 CONDITION OF DELIVERY

The different types of bricks shall be supplied as per sizes and drawings indicated at page number 5 and 6 of this specification.

- * Used to brick slag and metal zone of
 - 6.1: EAF of capacity of 10T and 30T
 - 6.2.1: VAD, VOD and LRF ladles
 - 6.2.2: Bottom bricks of VAD, VOD & LRF
 - 6.3: EAF of 70T
 - 6.4: Tap hole refractory for EBT of 70T EAF

4.0 COMPLIANCE WITH NATIONAL STANDARDS

There is no Indian standard of resin bonded Magnesia Carbon bricks.

5.0 PROPERTIES:

When tested in accordance with the relevant clauses of **IS-1528** or any other **International Standard/ Validated instrumental analysis traceable to international standards**, the test samples shall show the following values.

5.1: PHYSICAL PROPERTIES:

Bulk Density (gm /cc)	3	(Min)
Apparent Porosity	5%	(Max)
C.C.S (N/mm ²)	35	(Min)
Refractoriness Under Load	1600°C	(Min)
Thermal expansion up to 1400°C	2%	(Max)
HMOR, (Kg/Cm ²) AT 1400°C*30 minutes	125	(Min)

RMI	S.N GHOSH	WORKED BY	M.K SAHU
MPIC	A.K.KUSWAHA	CHECKED BY	SUNIL KUMAR
CHAIRMAN CPSC	V K AGARWAL	SUPERVIDED BY	P.K.ROY
APPROVED : PLANT STANDARDS COMMITTEE			
PREPARED : SMS TECH		ISSUED : Steel Melting Shop	DATE : 27-04-16



PLANT PURCHASE SPECIFICATION

(CFFP - HARDWAR)

FF 05066 Rev 5

Page 2 of 7

5.2 CHEMICAL COMPOSITION:

SL NO.	ELEMENTS	CONTENT	
		%(Min)	%(Max)
a)	MgO (in fused magnesia used)	97	
b)	MgO (in finished product)	82	
c)	Residual carbon (British cocking test)	8	12
d)	Al ₂ O ₃		2.0
e)	CaO		2.0
f)	SiO ₂		1.5
g)	Fe ₂ O ₃		0.5

6.0: TYPES OF BRICK.

	DESCRIPTION	SIZE	a mm	b mm	h mm	l mm	r mm	A deg
6.1	Bricks for Lining of 30t and 10T EAF	30/20	160	140	300	100	2100	-
		30/40	170	130	300	100	-	-
6.2.1	Bricks for side wall lining of ladles	SU 745	210	185.2	100	177.8	-	8
6.2.2	Bricks for bottom lining of ladles	Bottom Bricks	225	250	100	-	-	-

Drawing of bricks are given in page no 4

6.3: Bricks for lining of 70TEAF:

Quantity indicated below is for one set of lining

SI no	Bricks size	Quantity(Numbers)
1	400x190/110x100mm	150
2	400x170/130x100mm	500
3	400x160/140x100mm	360
4	350x170/130x100mm	100
5	350x160/140x100mm	342
6	400x150/100mm	402
7	350x150/100mm	128

(Dimensional tolerances: ±1.5% or 2mm which is greater)

WORKED
BY

M K SAHU

23/4/16

CHECKED
BY

SUNIL KR.

28/4/16

COPYRIGHT AND CONFIDENTIAL

The information on this document is the property of Bharat Heavy Electrical Limited It must not be used directly or indirectly in any way detrimental to the interest of the company

		PLANT PURCHASE SPECIFICATION (CFFP - HARDWAR)	FF 05066 Rev 5 Page 3 of 7			
		6.4. TAP HOLE REFRACTORIES FOR 70T EAF: Size and set as per drawing given at page no 5 of 7.				
COPYRIGHT AND CONFIDENTIAL The information on this documents is the property of Bharat Heavy Electricals Limited. It must not be used directly or indirectly in any way detrimental to the interest of the company.	7.0 INSPECTION AT SUPPLIER'S WORKS: - CFFP reserves the right to witness the testing of the material at supplier works and therefore the supplier shall notify the readiness of the material in advance. - CFFP may, at its discretion, test the material after receipt and acceptance of the material will be based on the CFFP's test results. <i>In case of any dispute in chemical analysis referee method shall be IS.</i> - For result of analysis and properties of material the decision of CFFP shall be final and binding on the supplier. 8.0 TEST CERTIFICATES: One Original and three copies of Test Certificate from the Manufacturer containing the following information along with test result of all properties given in clause no 5 should be provided. The T.C should contain the packing details of material. Manufacturer's Name Name of the material Batch/Lot No. Quantity. The TC should also contain the BHEL's P.O. No. and Challan No. and packing detail of the material.					
	9.0 PACKING AND MARKING: Packing should be such as to prevent loss / deterioration in quality during handling, transport and storage. It should be in the Manufacturer's packing. Each package should be marked with the following details. Name of the material Manufacturer's Name / Trade mark Batch/Lot No. Net weight.					
			WORKED BY CHECKED BY	MKSAHU SUNIL KR.		23/04/16 23/04/16



PLANT PURCHASE SPECIFICATION

(CFFP - HARDWAR)

10.0 PERFORMANCE OF MATERIAL:

Guaranteed heat in working lining (**Slag zone + Metal zone**) of EAF and VAD/VOD/LRF, under working conditions mentioned below against types of bricks.

Equipment.	Bricks	Working condition	LIFE
30T&10T EAF	30/20 & 30/40	Oxygen lancing, removal of P to 0.004%	80 heats minimum with intermediate repair near tap hole area and arch cooler area.
70T EAF	SET	Oxygen lancing, removal of P to 0.004%	25 Heats minimum
VAD/VOD/LRF Ladles	SU 745	Temp achieved-1720°C Max Degassing at Vacuum level ≤ 1 torr for ≈ 30 minutes	Minimum 5000 minutes of purging with one slag line repair.

Record of Life:

Furnace life → Record from **Heat Process Sheet/Furnace Log Book**.

Ladle life → Record from **Heat Process Sheet/Ladle Life Record Book** in pit side.

11.0 ACCEPTANCE OF MATERIAL:

Acceptance of material will be based on conditions defined in clause number 5 and 6 and drawings mentioned in page 5 and 6 of the specification.

WORKED
BY

M K SAHU

23/4/16

CHECKED
BY

SUNIL KR.

23/04/16




PLANT PURCHASE SPECIFICATION

(CFFP - HARDWAR)

FF 05066 Rev 5

Page 5 of 7

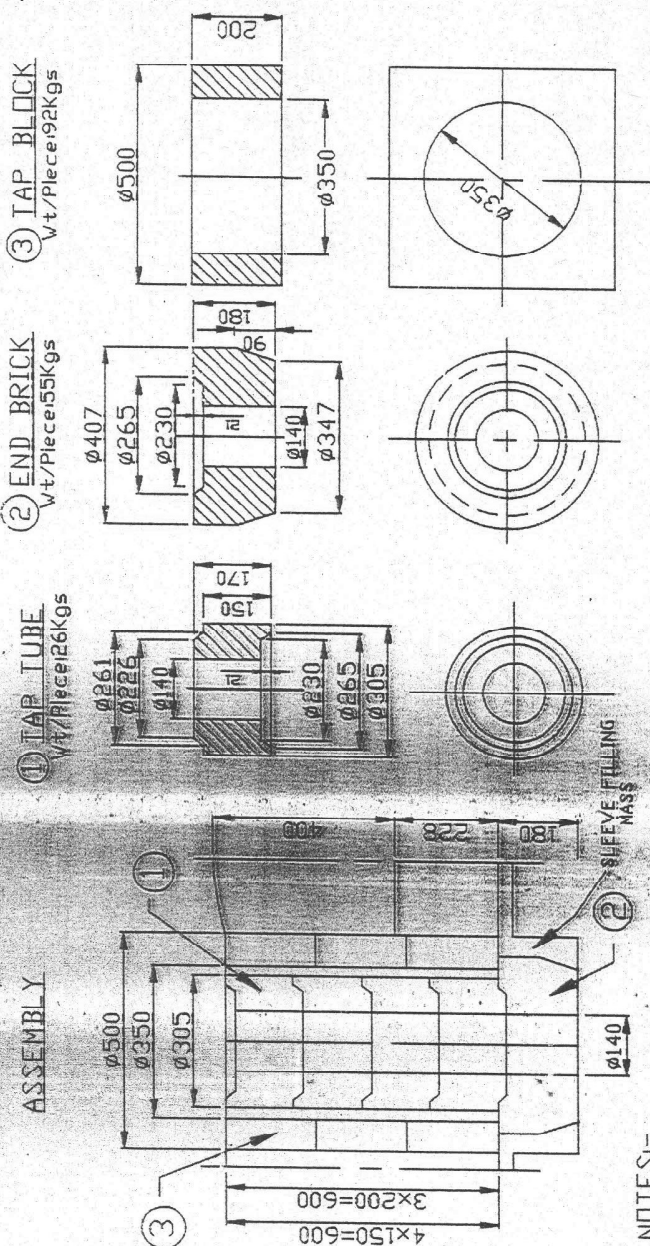

WORKED BY

M KSAHU

CHECKED BY

SUNIL KR.

[Signature]

23/4/16

[Signature]

23/04/16




PLANT PURCHASE SPECIFICATION

(CFFP - HARDWAR)


FF 05066 Rev 5

Page 6 of 7


COPYRIGHT AND CONFIDENTIAL
 The information on this document is the property of Bharat Heavy Electrical Limited It must not be used directly or indirectly in any way detrimental to the interest of the company

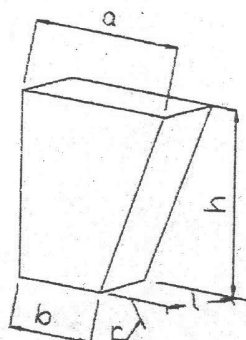

SIZE: 30/20 & 30/40

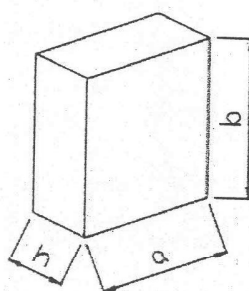

BOTTOM BRICK

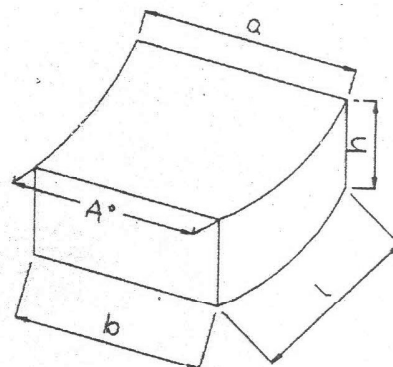

SIZE: SU 745

WORKED
BY

M KSAHU

23/4/16

CHECKED
BY

SUNIL KR.

28/04/16